

AD715252

# DAMAGE THRESHOLD STUDIES IN LASER CRYSTALS: EXPERIMENTAL AND THEORETICAL RESULTS IN RUBY AND SAPPHIRE

Contract No. DA-20-69-C-0277  
Project No. 0693

Contract No. DA-20-69-C-0277  
Project No. 0693

Contract No. DA-20-69-C-0277  
Project No. 0693  
Contract No. DA-20-69-C-0277  
Project No. 0693

Contract No. DA-20-69-C-0277  
Project No. 0693

## SEMI-ANNUAL REPORT NO. 2 JULY 1970

THIS DOCUMENT HAS BEEN APPROVED FOR PUBLIC  
RELEASE AND SALE; ITS DISTRIBUTION IS UNLIMITED

Contract Monitor C Martin Stickley  
OPTICAL PHYSICS LABORATORY

Sponsored by  
Advanced Research Projects Agency  
ARPA Order No. 1434  
Monitored by

AIR FORCE CAMBRIDGE RESEARCH LABORATORIES  
AIR FORCE SYSTEMS COMMAND  
UNITED STATES AIR FORCE  
BEDFORD, MASSACHUSETTS 01730

DDC  
RECEIVED  
JUL 18 1970  
C

Reproduced by  
NATIONAL TECHNICAL  
INFORMATION SERVICE  
Springfield, Va 22151

**BEST  
AVAILABLE COPY**

SECRET

ADVANCED RESEARCH PROJECTS AGENCY  
CONTRACT NO. F19620-69-C-0277  
PROJECT NO. 8691

Raytheon Research Laboratories  
Raytheon Aircraft Company  
7011 Malibu Canyon Road  
Malibu, California 90263

Contract No. F19620-69-C-0277  
Project No. 8691


Semi-Annual Report No. 2

July 1970

This document has been approved for public  
Release and Sale; its distribution is unlimited.

Contract Monitor: C. Martin Stickley  
Optical Physics Laboratory

Sponsored by  
Advanced Research Projects Agency  
ARPA Order No. 1434  
Monitored by  
AIR FORCE CAMBRIDGE RESEARCH LABORATORIES  
AIR FORCE SYSTEMS COMMAND  
UNITED STATES AIR FORCE  
BEDFORD, MASSACHUSETTS 01730

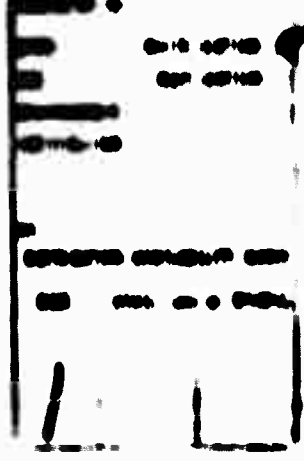

1. 1960  
2. 1961  
3. 1962  
4. 1963  
5. 1964  
6. 1965  
7. 1966  
8. 1967  
9. 1968  
10. 1969  
11. 1970  
12. 1971  
13. 1972  
14. 1973  
15. 1974  
16. 1975  
17. 1976  
18. 1977  
19. 1978  
20. 1979  
21. 1980  
22. 1981  
23. 1982  
24. 1983  
25. 1984  
26. 1985  
27. 1986  
28. 1987  
29. 1988  
30. 1989  
31. 1990  
32. 1991  
33. 1992  
34. 1993  
35. 1994  
36. 1995  
37. 1996  
38. 1997  
39. 1998  
40. 1999  
41. 2000  
42. 2001  
43. 2002  
44. 2003  
45. 2004  
46. 2005  
47. 2006  
48. 2007  
49. 2008  
50. 2009  
51. 2010  
52. 2011  
53. 2012  
54. 2013  
55. 2014  
56. 2015  
57. 2016  
58. 2017  
59. 2018  
60. 2019  
61. 2020  
62. 2021  
63. 2022  
64. 2023  
65. 2024  
66. 2025  
67. 2026  
68. 2027  
69. 2028  
70. 2029  
71. 2030  
72. 2031  
73. 2032  
74. 2033  
75. 2034  
76. 2035  
77. 2036  
78. 2037  
79. 2038  
80. 2039  
81. 2040  
82. 2041  
83. 2042  
84. 2043  
85. 2044  
86. 2045  
87. 2046  
88. 2047  
89. 2048  
90. 2049  
91. 2050  
92. 2051  
93. 2052  
94. 2053  
95. 2054  
96. 2055  
97. 2056  
98. 2057  
99. 2058  
100. 2059  
101. 2060  
102. 2061  
103. 2062  
104. 2063  
105. 2064  
106. 2065  
107. 2066  
108. 2067  
109. 2068  
110. 2069  
111. 2070  
112. 2071  
113. 2072  
114. 2073  
115. 2074  
116. 2075  
117. 2076  
118. 2077  
119. 2078  
120. 2079  
121. 2080  
122. 2081  
123. 2082  
124. 2083  
125. 2084  
126. 2085  
127. 2086  
128. 2087  
129. 2088  
130. 2089  
131. 2090  
132. 2091  
133. 2092  
134. 2093  
135. 2094  
136. 2095  
137. 2096  
138. 2097  
139. 2098  
140. 2099  
141. 2100  
142. 2101  
143. 2102  
144. 2103  
145. 2104  
146. 2105  
147. 2106  
148. 2107  
149. 2108  
150. 2109  
151. 2110  
152. 2111  
153. 2112  
154. 2113  
155. 2114  
156. 2115  
157. 2116  
158. 2117  
159. 2118  
160. 2119  
161. 2120  
162. 2121  
163. 2122  
164. 2123  
165. 2124  
166. 2125  
167. 2126  
168. 2127  
169. 2128  
170. 2129  
171. 2130  
172. 2131  
173. 2132  
174. 2133  
175. 2134  
176. 2135  
177. 2136  
178. 2137  
179. 2138  
180. 2139  
181. 2140  
182. 2141  
183. 2142  
184. 2143  
185. 2144  
186. 2145  
187. 2146  
188. 2147  
189. 2148  
190. 2149  
191. 2150  
192. 2151  
193. 2152  
194. 2153  
195. 2154  
196. 2155  
197. 2156  
198. 2157  
199. 2158  
200. 2159  
201. 2160  
202. 2161  
203. 2162  
204. 2163  
205. 2164  
206. 2165  
207. 2166  
208. 2167  
209. 2168  
210. 2169  
211. 2170  
212. 2171  
213. 2172  
214. 2173  
215. 2174  
216. 2175  
217. 2176  
218. 2177  
219. 2178  
220. 2179  
221. 2180  
222. 2181  
223. 2182  
224. 2183  
225. 2184  
226. 2185  
227. 2186  
228. 2187  
229. 2188  
230. 2189  
231. 2190  
232. 2191  
233. 2192  
234. 2193  
235. 2194  
236. 2195  
237. 2196  
238. 2197  
239. 2198  
240. 2199  
241. 2200  
242. 2201  
243. 2202  
244. 2203  
245. 2204  
246. 2205  
247. 2206  
248. 2207  
249. 2208  
250. 2209  
251. 2210  
252. 2211  
253. 2212  
254. 2213  
255. 2214  
256. 2215  
257. 2216  
258. 2217  
259. 2218  
260. 2219  
261. 2220  
262. 2221  
263. 2222  
264. 2223  
265. 2224  
266. 2225  
267. 2226  
268. 2227  
269. 2228  
270. 2229  
271. 2230  
272. 2231  
273. 2232  
274. 2233  
275. 2234  
276. 2235  
277. 2236  
278. 2237  
279. 2238  
280. 2239  
281. 2240  
282. 2241  
283. 2242  
284. 2243  
285. 2244  
286. 2245  
287. 2246  
288. 2247  
289. 2248  
290. 2249  
291. 2250  
292. 2251  
293. 2252  
294. 2253  
295. 2254  
296. 2255  
297. 2256  
298. 2257  
299. 2258  
300. 2259  
301. 2260  
302. 2261  
303. 2262  
304. 2263  
305. 2264  
306. 2265  
307. 2266  
308. 2267  
309. 2268  
310. 2269  
311. 2270  
312. 2271  
313. 2272  
314. 2273  
315. 2274  
316. 2275  
317. 2276  
318. 2277  
319. 2278  
320. 2279  
321. 2280  
322. 2281  
323. 2282  
324. 2283  
325. 2284  
326. 2285  
327. 2286  
328. 2287  
329. 2288  
330. 2289  
331. 2290  
332. 2291  
333. 2292  
334. 2293  
335. 2294  
336. 2295  
337. 2296  
338. 2297  
339. 2298  
340. 2299  
341. 2300  
342. 2301  
343. 2302  
344. 2303  
345. 2304  
346. 2305  
347. 2306  
348. 2307  
349. 2308  
350. 2309  
351. 2310  
352. 2311  
353. 2312  
354. 2313  
355. 2314  
356. 2315  
357. 2316  
358. 2317  
359. 2318  
360. 2319  
361. 2320  
362. 2321  
363. 2322  
364. 2323  
365. 2324  
366. 2325  
367. 2326  
368. 2327  
369. 2328  
370. 2329  
371. 2330  
372. 2331  
373. 2332  
374. 2333  
375. 2334  
376. 2335  
377. 2336  
378. 2337  
379. 2338  
380. 2339  
381. 2340  
382. 2341  
383. 2342  
384. 2343  
385. 2344  
386. 2345  
387. 2346  
388. 2347  
389. 2348  
390. 2349  
391. 2350  
392. 2351  
393. 2352  
394. 2353  
395. 2354  
396. 2355  
397. 2356  
398. 2357  
399. 2358  
400. 2359  
401. 2360  
402. 2361  
403. 2362  
404. 2363  
405. 2364  
406. 2365  
407. 2366  
408. 2367  
409. 2368  
410. 2369  
411. 2370  
412. 2371  
413. 2372  
414. 2373  
415. 2374  
416. 2375  
417. 2376  
418. 2377  
419. 2378  
420. 2379  
421. 2380  
422. 2381  
423. 2382  
424. 2383  
425. 2384  
426. 2385  
427. 2386  
428. 2387  
429. 2388  
430. 2389  
431. 2390  
432. 2391  
433. 2392  
434. 2393  
435. 2394  
436. 2395  
437. 2396  
438. 2397  
439. 2398  
440. 2399  
441. 2400  
442. 2401  
443. 2402  
444. 2403  
445. 2404  
446. 2405  
447. 2406  
448. 2407  
449. 2408  
450. 2409  
451. 2410  
452. 2411  
453. 2412  
454. 2413  
455. 2414  
456. 2415  
457. 2416  
458. 2417  
459. 2418  
460. 2419  
461. 2420  
462. 2421  
463. 2422  
464. 2423  
465. 2424  
466. 2425  
467. 2426  
468. 2427  
469. 2428  
470. 2429  
471. 2430  
472. 2431  
473. 2432  
474. 2433  
475. 2434  
476. 2435  
477. 2436  
478. 2437  
479. 2438  
480. 2439  
481. 2440  
482. 2441  
483. 2442  
484. 2443  
485. 2444  
486. 2445  
487. 2446  
488. 2447  
489. 2448  
490. 2449  
491. 2450  
492. 2451  
493. 2452  
494. 2453  
495. 2454  
496. 2455  
497. 2456  
498. 2457  
499. 2458  
500. 2459  
501. 2460  
502. 2461  
503. 2462  
504. 2463  
505. 2464  
506. 2465  
507. 2466  
508. 2467  
509. 2468  
510. 2469  
511. 2470  
512. 2471  
513. 2472  
514. 2473  
515. 2474  
516. 2475  
517. 2476  
518. 2477  
519. 2478  
520. 2479  
521. 2480  
522. 2481  
523. 2482  
524. 2483  
525. 2484  
526. 2485  
527. 2486  
528. 2487  
529. 2488  
530. 2489  
531. 2490  
532. 2491  
533. 2492  
534. 2493  
535. 2494  
536. 2495  
537. 2496  
538. 2497  
539. 2498  
540. 2499  
541. 2500  
542. 2501  
543. 2502  
544. 2503  
545. 2504  
546. 2505  
547. 2506  
548. 2507  
549. 2508  
550. 2509  
551. 2510  
552. 2511  
553. 2512  
554. 2513  
555. 2514  
556. 2515  
557. 2516  
558. 2517  
559. 2518  
560. 2519  
561. 2520  
562. 2521  
563. 2522  
564. 2523  
565. 2524  
566. 2525  
567. 2526  
568. 2527  
569. 2528  
570. 2529  
571. 2530  
572. 2531  
573. 2532  
574. 2533  
575. 2534  
576. 2535  
577. 2536  
578. 2537  
579. 2538  
580. 2539  
581. 2540  
582. 2541  
583. 2542  
584. 2543  
585. 2544  
586. 2545  
587. 2546  
588. 2547  
589. 2548  
590. 2549  
591. 2550  
592. 2551  
593. 2552  
594. 2553  
595. 2554  
596. 2555  
597. 2556  
598. 2557  
599. 2558  
600. 2559  
601. 2560  
602. 2561  
603. 2562  
604. 2563  
605. 2564  
606. 2565  
607. 2566  
608. 2567  
609. 2568  
610. 2569  
611. 2570  
612. 2571  
613. 2572  
614. 2573  
615. 2574  
616. 2575  
617. 2576  
618. 2577  
619. 2578  
620. 2579  
621. 2580  
622. 2581  
623. 2582  
624. 2583  
625. 2584  
626. 2585  
627. 2586  
628. 2587  
629. 2588  
630. 2589  
631. 2590  
632. 2591  
633. 2592  
634. 2593  
635. 2594  
636. 2595  
637. 2596  
638. 2597  
639. 2598  
640. 2599  
641. 2600  
642. 2601  
643. 2602  
644. 2603  
645. 2604  
646. 2605  
647. 2606  
648. 2607  
649. 2608  
650. 2609  
651. 2610  
652. 2611  
653. 2612  
654. 2613  
655. 2614  
656. 2615  
657. 2616  
658. 2617  
659. 2618  
660. 2619  
661. 2620  
662. 2621  
663. 2622  
664. 2623  
665. 2624  
666. 2625  
667. 2626  
668. 2627  
669. 2628  
670. 2629  
671. 2630  
672. 2631  
673. 2632  
674. 2633  
675. 2634  
676. 2635  
677. 2636  
678. 2637  
679. 2638  
680. 2639  
681. 2640  
682. 2641  
683. 2642  
684. 2643  
685. 2644  
686. 2645  
687. 2646  
688. 2647  
689. 2648  
690. 2649  
691. 2650  
692. 2651  
693. 2652  
694. 2653  
695. 2654  
696. 2655  
697. 2656  
698. 2657  
699. 2658  
700. 2659  
701. 2660  
702. 2661  
703. 2662  
704. 2663  
705. 2664  
706. 2665  
707. 2666  
708. 2667  
709. 2668  
710. 2669  
711. 2670  
712. 2671  
713. 2672  
714. 2673  
715. 2674  
716. 2675  
717. 2676  
718. 2677  
719. 2678  
720. 2679  
721. 2680  
722. 2681  
723. 2682  
724. 2683  
725. 2684  
726. 2685  
727. 2686  
728. 2687  
729. 2688  
730. 2689  
731. 2690  
732. 2691  
733. 2692  
734. 2693  
735. 2694  
736. 2695  
737. 2696  
738. 2697  
739. 2698  
740. 2699  
741. 2700  
742. 2701  
743. 2702  
744. 2703  
745. 2704  
746. 2705  
747. 2706  
748. 2707  
749. 2708  
750. 2709  
751. 2710  
752. 2711  
753. 2712  
754. 2713  
755. 2714  
756. 2715  
757. 2716  
758. 2717  
759. 2718  
760. 2719  
761. 2720  
762. 2721  
763. 2722  
764. 2723  
765. 2724  
766. 2725  
767. 2726  
768. 2727  
769. 2728  
770. 2729  
771. 2730  
772. 2731  
773. 2732  
774. 2733  
775. 2734  
776. 2735  
777. 2736  
778. 2737  
779. 2738  
780. 2739  
781. 2740  
782. 2741  
783. 2742  
784. 2743  
785. 2744  
786. 2745  
787. 2746  
788. 2747  
789. 2748  
790. 2749  
791. 2750  
792. 2751  
793. 2752  
794. 2753  
795. 2754  
796. 2755  
797. 2756  
798. 2757  
799. 2758  
800. 2759  
801. 2760  
802. 2761  
803. 2762  
804. 2763  
805. 2764  
806. 2765  
807. 2766  
808. 2767  
809. 2768  
810. 2769  
811. 2770  
812. 2771  
813. 2772  
814. 2773  
815. 2774  
816. 2775  
817. 2776  
818. 2777  
819. 2778  
820. 2779  
821. 2780  
822. 2781  
823. 2782  
824. 2783  
825. 2784  
826. 2785  
827. 2786  
828. 2787  
829. 2788  
830. 2789  
831. 2790  
832. 2791  
833. 2792  
834. 2793  
835. 2794  
836. 2795  
837. 2796  
838. 2797  
839. 2798  
840. 2799  
841. 2800  
842. 2801  
843. 2802  
844. 2803  
845. 2804  
846. 2805  
847. 2806  
848. 2807  
849. 2808  
850. 2809  
851. 2810  
852. 2811  
853. 2812  
854. 2813  
855. 2814  
856. 2815  
857. 2816  
858. 2817  
859. 2818  
860. 2819  
861. 2820  
862. 2821  
863. 2822  
864. 2823  
865. 2824  
866. 2825  
867. 2826  
868. 2827  
869. 2828  
870. 2829  
871. 2830  
872. 2831  
873. 2832  
874. 2833  
875. 2834  
876. 2835  
877. 2836  
878. 2837  
879. 2838  
880. 2839  
881. 2840  
882. 2841  
883. 2842  
884. 2843  
885. 2844  
886. 2845  
887. 2846  
888. 2847  
889. 2848  
890. 2849  
891. 2850  
892. 2851  
893. 2852  
894. 2853  
895. 2854  
896. 2855  
897. 2856  
898. 2857  
899. 2858  
900. 2859  
901. 2860  
902. 2861  
903. 2862  
904. 2863  
905. 2864  
906. 2865  
907. 2866  
908. 2867  
909. 2868  
910. 2869  
911. 2870  
912. 2871  
913. 2872  
914. 2873  
915. 2874  
916. 2875  
917. 2876  
918. 2877  
919. 2878  
920. 2879  
921. 2880  
922. 2881  
923. 2882  
924. 2883  
925. 2884  
926. 2885  
927. 2886  
928. 2887  
929. 2888  
930. 2889  
931. 2890  
932. 2891  
933. 2892  
934. 2893  
935. 2894  
936. 2895  
937. 2896  
938. 2897  
939. 2898  
940. 2899  
941. 2900  
942. 2901  
943. 2902  
944. 2903  
945. 2904  
946. 2905  
947. 2906  
948. 2907  
949. 2908  
950. 2909  
951. 2910  
952. 2911  
953. 2912  
954. 2913  
955. 2914  
956. 2915  
957. 2916  
958. 2917  
959. 2918  
960. 2919  
961. 2920  
962. 2921  
963. 2922  
964. 2923  
965. 2924  
966. 2925  
967. 2926  
968. 2927  
969. 2928  
970. 2929  
971. 2930  
972. 2931  
973. 2932  
974. 2933  
975. 2934  
976. 2935  
977. 2936  
978. 2937  
979. 2938  
980. 2939  
981. 2940  
982. 2941  
983. 2942  
984. 2943  
985. 2944  
986. 2945  
987. 2946  
988. 2947  
989. 2948  
990. 2949  
991. 2950  
992. 2951  
993. 2952  
994. 2953  
995. 2954  
996. 2955  
997. 2956  
998. 2957  
999. 2958  
1000. 2959  
1001. 2960  
1002. 2961  
1003. 2962  
1004. 2963  
1005. 2964  
1006. 2965  
1007. 2966  
1008. 2967  
1009. 2968  
1010. 2969  
1011. 2970  
1012. 2971  
1013. 2972  
1014. 2973  
1015. 2974  
1016. 2975  
1017. 2976  
1018. 2977  
1019. 2978  
1020. 2979  
1021. 2980  
1022. 2981  
1023. 2982  
1024. 2983  
1025. 2984  
1026. 2985  
1027. 2986  
1028. 2987  
1029. 2988  
1030. 2989  
1031. 2990  
1032. 2991  
1033. 2992  
1034. 2993  
1035. 2994  
1036. 2995  
1037. 2996  
1038. 2997  
1039. 2998  
1040. 2999  
1041. 3000  
1042. 3001  
1043. 3002  
1044. 3003  
1045. 3004  
1046. 3005  
1047. 3006  
1048. 3007  
1049. 3008  
1050. 3009  
1051. 3010  
1052. 3011  
1053. 3012  
1054. 3013  
1055. 3014  
1056. 3015  
1057. 3016  
1058. 3017  
1059. 3018  
1060. 3019  
1061. 3020  
1062. 3021  
1063. 3022  
1064. 3023  
1065. 3024  
1066. 3025  
1067. 3026  
1068. 3027  
1069. 3028  
1070. 3029  
1071. 3030  
1072. 3031  
1073. 3032  
1074. 3033  
1075. 3034  
1076. 3035  
1077. 3036  
1078. 3037  
1079. 3038  
1080. 3039  
1081. 3040  
1082. 3041  
1083. 3042  
1084. 3043  
1085. 3044  
1086. 3045  
1087. 3046  
1088. 3047  
1089. 3048  
1090. 3049  
1091. 3050  
1092. 3051  
1093. 3052  
1094. 3053  
1095. 3054  
1096. 3055  
1097. 3056  
1098. 3057  
1099. 3058  
1100. 3059  
1101. 3060  
1102. 3061  
1103. 3062  
1104. 3063  
1105. 3064  
1106. 3065  
1107. 3066  
1108. 3067  
1109. 3068  
1110. 3069  
1111. 3070  
1112. 3071  
1113. 3072  
1114. 3073  
1115. 3074  
1116. 3075  
1117. 3076  
11

## ABSTRACT

In this report the results of a number of experiments are presented as well as a summary of the theoretical work. Bulk damage thresholds for several ruby and sapphire samples from different sources are presented. The problem of surface damage is discussed, and qualitative comparisons between entrance and exit surface damage are made. Differences between the gross characteristics of bulk damage in ruby and sapphire are presented and discussed. The dependence of damage threshold on  $\text{TiO}_2$  doping and optical pumping is presented. The unexpected results are discussed and further experiments proposed. The theoretical treatment deals with processes by which "cold" conduction electrons may damage the lattice before they gain enough energy to ionize their surroundings. It is shown that the energy that the conduction electrons absorb linearly from the optical beam is deposited almost immediately in the lattice and is of sufficient magnitude to form a rupturing shock wave. It is also shown that the photoexcitation of impurity levels is enhanced by the presence of conduction electrons. The presence of conduction electrons and excited impurities is likely to alter the refractive index significantly and affect the focusing (self- or external) in a complicated way. Implications of these results for raising damage thresholds are discussed.

## TABLE OF CONTENTS

	LIST OF ILLUSTRATIONS . . . . .	vii
I.	EXPERIMENTAL STUDIES ON OPTICAL DAMAGE . . . . .	1
A.	Introduction and Summary of Results . . . . .	1
B.	Experimental Apparatus . . . . .	1
C.	Power and Energy Measurements . . . . .	4
D.	Gross Characteristics of Damage . . . . .	6
E.	Damage Threshold Experiments . . . . .	18
F.	Dependence of Damage Threshold on Added $\text{TiO}_2$ . . . . .	21
G.	Optical Pumping Experiments . . . . .	23
H.	Plans for Next Period . . . . .	28
II.	THEORETICAL STUDIES ON OPTICAL DAMAGE . . . . .	31
A.	Introduction . . . . .	31
B.	A Proposed General Outline of Optical Damage in Sapphire and Ruby . . . . .	31
C.	The Role of Photoelectrons in Crystal Damage . . . . .	34
	APPENDIX - Role of Photo- Electrons in Optical Damage . . . . .	37

## LIST OF ILLUSTRATIONS

Fig. 1.	Schematic representation of experimental apparatus . . . . .	2
Fig. 2.	Typical photo monitoring Fabry-Perot interferogram, near-field, and far-field beam patterns . . . . .	5
Fig. 3.	Tektronix 519 oscilloscope traces of laser output with 20 nsec/division sweep rate . . . . .	5
Fig. 4.	Photographs of ruby samples while being subjected to laser radiation . . . . .	8
Fig. 5.	Exit (right) and entrance (left) surfaces of damaged ruby sample . . . . .	9
Fig. 6.	Exit (right) and entrance (left) surfaces of damaged ruby sample . . . . .	11
Fig. 7.	Magnified view of entrance surface damage such as seen in Figs. 5 and 6 . . . . .	12
Fig. 8.	Photomicrographs of exit surface damage pits and crazing . . . . .	13
Fig. 9.	Scanning electron micrograph of exit surface damage in ruby showing crazed region and surface pitting . . . . .	14
Fig. 10.	Photomicrograph of damage tracks in ruby . . . . .	16
Fig. 11.	Photomicrograph of damage tracks in sapphire . . . . .	16
Fig. 12.	Bulk damage thresholds for a number of ruby and sapphire samples . . . . .	19
Fig. 13.	Absorption spectra of Verneuil sapphire whose thresholds are reported in Table II . . . . .	22
Fig. 14.	Apparatus used for optical pumping experiments . . . . .	24

Fig. 15.	Relative bulk damage threshold as a function of optical pumping for different samples . . . . .	25
Fig. 16.	Location of beginning of damage tracks from entrance surface versus optical pumping energy for ruby samples . . . . .	27
Fig. 17.	Location of beginning of damage tracks from entrance surface versus laser power incident on 19 cm lens . . . . .	29




## **EXPERIMENTAL STUDIES ON OPTICAL DAMAGE**

### **A. Introduction and Summary of Results**

The experimental work during this reporting period has been devoted to a number of different areas. We have modified and improved the ruby laser so that it operates very reliably (95%) in a single mode. This has been accomplished by the use of a temperature controlled resonant reflector : 2 mm aperture and a dye Q-switch. Extensive energy calibrations have been carried out using different calibrated detectors giving us a more reasonable measure of the uncertainty in our output. Bulk damage threshold measurements have been carried out for a number of ruby and sapphire samples obtained from different sources. Damage at both entrance and exit surfaces has been examined and certain comparisons are made. The differences between the gross characteristics of bulk damage in ruby and sapphire are presented and discussed. The effect on damage threshold of  $\text{TiO}_2$  doping has been studied for both ruby and sapphire, and a pronounced lowering of threshold was found (contrary to previously reported results). We have carried out a few experiments in which the damage threshold was measured as a function of optical pumping for both ruby and sapphire. The unexpected results are discussed and further experiments proposed.

### **B. Experimental Apparatus**

The apparatus used in the damage threshold experiments is essentially the same as that described in the previous report (Semi-Annual Report No. 1), and only the modifications will be described. A schematic representation of the apparatus is shown in Fig. 1. The main difference between this apparatus and that shown previously is the use of a dye Q-switch in place of the rotating prism in the laser. We use a solution of cryptocyanine in methanol in a 1 mm pathlength cell the optical transmission of which is 30% at 6943 Å. Another feature not shown in the first apparatus is the  $\text{MgO}$  diffuser placed after the sample and the associated monitoring detector. The signals from this detector and the one which detects the light reflected from beamsplitter  $B_2$  are integrated and displayed on a Tektronix 555 dual-beam oscilloscope. In addition, beam splitter  $B_2$  has been rotated so that the light is incident much closer

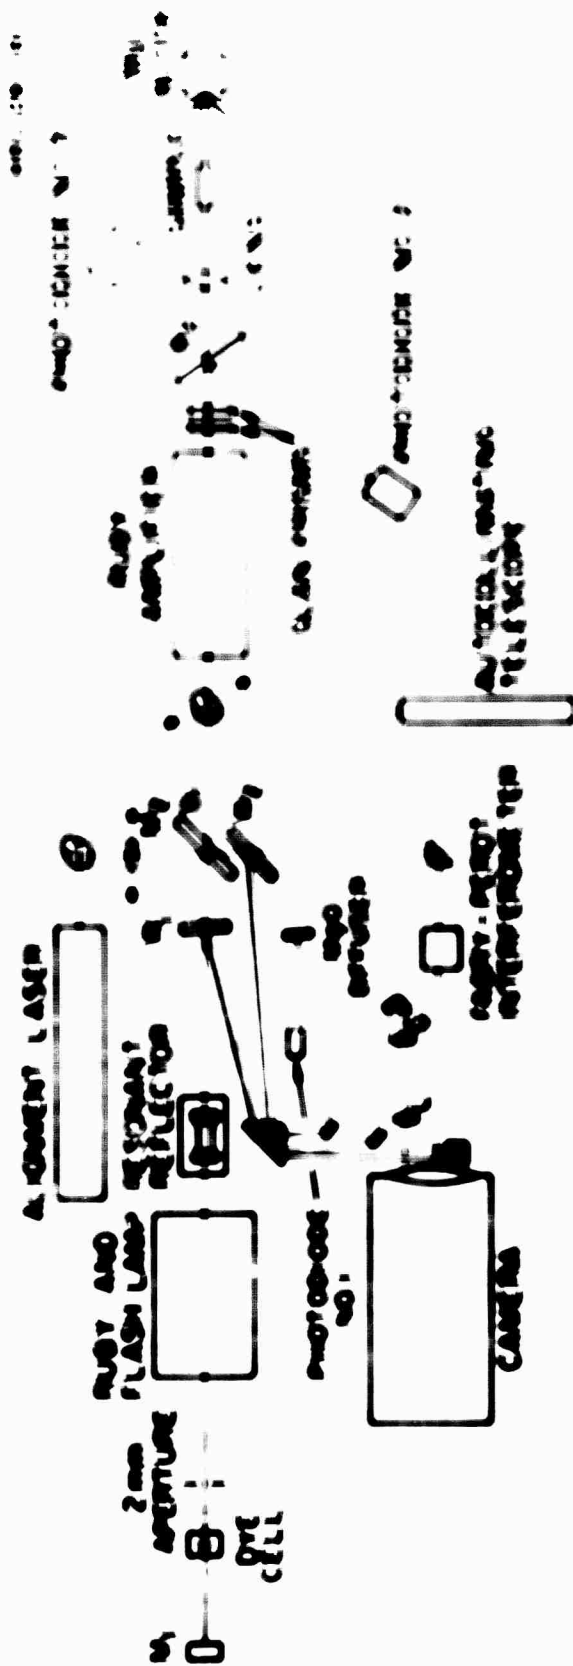[illegible]

to the system that is the objective being. At first we had used a lens to focus the light. The protection of the lens to the light from the laser is not the same as the total amount of light reflected from the laser beam. However, there was a great deal of scattered light from the laser beam of which only a small part was collected. This was not completely true. The reason for this was not completely clear, and we suspected that there may have been small changes in the angle of reflection on the sample itself. Due to, perhaps, slight differences in laser alignment from shot to shot. This would result in appreciable changes in the total amount of light reflected into the detector. When the beam splitter was introduced for smaller angles of incidence where the reflectivity is fairly independent of angle, the problem disappeared. Another feature slightly different from the earlier setup is that photodiode No. 1 looks at the light reflected through a ground glass screen located about 6 in. away. Earlier the screen was much closer (1.5 ft). With this adjustment the signal from the photodiode is much less sensitive to slight changes in position on the ground glass screen which might result from small changes in alignment of the laser.

The two scan systems shown in Fig. 1 as variable attenuators have not yet been used for that purpose, since we wished to minimize excitation losses in our beam because we often did not have sufficient pump to cause damage with the long focal length (80 in) lens. Instead we have varied the pumping time in the amplifier to obtain variations in output power.

One feature of the system as it now exists which leaves something to be desired is the appreciable fluctuation in the power output from the laser. In spite of the fact that the mode properties are very well behaved the power output is apparently very critically dependent on alignment and flash lamp voltage and has been known to change by as much as 10% from shot to shot with no apparent difference in either of the above parameters. Another feature

For example, at  $\theta = 32^\circ$  a change of  $1^\circ$  gives a 100% change in the reflection coefficient whereas at  $\theta = 16^\circ$  the same angular change results in only 1.5% change in reflection coefficient.

All lenses used for focusing the laser into the samples are designed for minimum spherical aberration and antireflection coated. They were obtained from Special Optics.

of the oscillator is that for lower energy pulses the duration of the pulses increases. Thus the pulse length can vary between about 15 and 25 nsec. We plan to monitor the pump voltage more accurately to see if this improves reproducibility.

We present samples of the data obtained with each shot of the oscillator. Figure 2 shows an example of what we see with our monitoring camera, and Fig. 3 shows a time trace of the laser output taken with photodiode No. 1 and displayed on the Tektronix 519 oscilloscope. Figure 3(a) shows the smooth temporal shape seen about 95% of the time, while Fig. 3(b) shows an extreme example of multimode oscillation. In this case two modes are oscillating with a frequency separation of 750 MHz. This frequency corresponds to the spacing between the end of the ruby and the resonant reflector. The overlapping spectral ranges of the Fabry-Perot interferometer<sup>2</sup> and the 519 oscilloscope insure that the oscillation of anything other than a single longitudinal mode will be detected.

The amplifier is essentially the same as that described in the previous report except that a modification in the lamp design was made. The reason for this is that the impedance match between the lamp and the pulse-forming network is not optimum. This results in some reflection in the transmission line so that the sample is not pumped as effectively as it could be. The new lamp which has not yet been tested should improve the impedance match and permit more efficient pumping. The maximum gain obtained with the amplifier is about 10 dB. The characteristics of our laser are summarized in Table 1.

### C. Power and Energy Measurements

Early in this reporting period we discovered that the primary reference used as a power standard in the first measurements (a Korad biplanar photodiode) showed a drastic change in photoresponse. The reason for this is not known. As a result some doubt was cast on the initial power calibration figures. We proceeded to obtain three separate "calibrated" detectors and used them to establish a new standard for photodiode No. 2, our energy monitor. Of these three detectors, two were TRG calibrated thermopiles and the third was a photodiode which had been checked against a number of other calibrated detectors from different sources.

<sup>2</sup>The Fabry-Perot interferometer has a 3.17 mm spacer giving a free spectral range of  $1.58 \text{ cm}^{-1}$ . We have measured the resolution to be better than  $0.06 \text{ cm}^{-1}$  or 1.8 GHz.


HRL 264-7



Fig. 2.  
Typical photo monitoring Fabry-Perot interferogram, near-field, and far-field beam patterns. The difference in optical density between the two halves of the picture is N.D. 0.6. The free spectral range of the interferometer is  $1.6 \text{ cm}^{-1}$ .

HRL 265-5

a

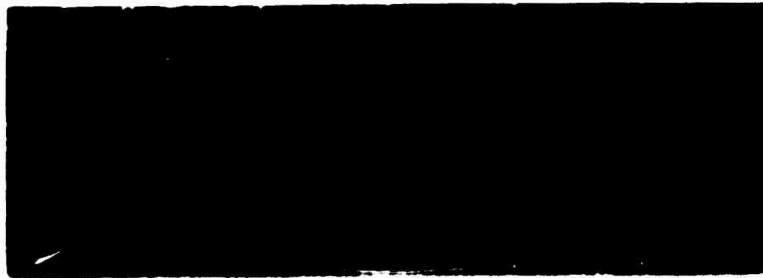

b



Fig. 3. Tektronix 519 oscilloscope traces of laser output with 20 nsec/division sweep rate. (a) Smooth pulse observed  $\sim 95\%$  of the time. (b) Modulated pulse ( $\sim 750 \text{ MHz}$ ).

TABLE I  
Characteristics of Ruby Laser

Energy Output	12 - 15 mJ
Pulse Length	$\sim 20$ nsec
Peak Power	0.6 - 0.8 MW
Beam Radius (1/e for E field)	1 mm ( $\pm 10\%$ )
Beam Divergence	$0.6 \pm 0.1$ mrad (full angle)
Calculated Beam Divergence	0.44 mrad (full angle)

T39

In these experiments the laser and amplifier were fired and signals from the calibrated detectors were compared with that from photodiode No. 2 (Fig. 1). A series of measurements was also taken in which the amplifier was not in place and where both photodiodes No. 1 and No. 2 were compared with the standard detector. In these cases the 519 traces from photodiode No. 1 were integrated, and the integral was compared with the other signals.

The precision of these measurements was very good ( $\sim 5\%$ ) for each standard detector taken by itself but the three calibrations were not in agreement, the two extremes differing by about 30%. Since our precision is much better than this, we can expect a more accurate power calibration than we obtained at that time. The two thermopiles were sent back to TRG for recalibration. When they return the measurement will be repeated.

#### D. Gross Characteristics of Damage

We now wish to point out some of the qualitative features of the damage we have observed in ruby and sapphire, and point out the various differences seen in bulk and surface damage.

When we place these samples in the beam we often see some plasma formation at the entrance and exit surfaces; this is shown in Fig. 4(a). In this shot no internal damage was formed, but a small pit was visible at the exit surface.


We wish to emphasize here that exit surface damage is the first to appear in most of our measurements and that the threshold for exit surface damage is about an order of magnitude lower than that for bulk damage. We also notice that the plasma formed at the exit surface is often irregular, sometimes with a pointed appearance in the direction of light propagation; the plasma formed at the entrance surface is more rounded in appearance. Figure 4(b) shows a photograph of another sample in which internal as well as exit surface damage was formed. Here we see a damage track beginning about a third of the way in from the entrance surface. Notice also the flaring out of the beam past the damage track. This blowing up of the beam, discussed briefly in the last report, could be caused by a scattering of light from the damage sites or perhaps by self-focusing and subsequent diffraction. If we assume that the fanning out of the beam is caused by diffraction from a self-focused spot, we can determine roughly the spot size by measuring the angle of the fanned out part of the beam. A crude measurement gives  $7 \times 10^{-2}$  rad for the half-angle, which corresponds to a self-focused spot whose diameter is  $6.3 \mu\text{m}$ . This is not an unrealistically small spot size for self-focusing, and thus the flared out beam could arise from that. On the other hand, we notice that the flared out part of the beam is not very uniform in that the center part has much more light than the outer portions. This would suggest scattering from the damage sites in which a small part of the beam is deflected while most of it continues along the same path.

## 1. Surface Damage

The difference in the qualitative features of entrance and exit surfaces will be discussed briefly in this section. Figure 5 shows photographs of both the entrance and exit faces of a ruby rod subjected to varying amounts of laser radiation. Note the difference in the kind of damage seen. The exit surface generally shows definite crater formation as was discussed in the last report and illustrated with a number of scanning electron micrographs. The entrance surface on the other hand shows relatively little material lost from the surface.


The influence of entrance surface damage on the apparent threshold for bulk damage has come to our attention during this reporting period. It is possible that one reason for the large fluctuation (see Section I-E) observed in the bulk damage threshold is the generation of damage at the entrance surface and subsequent scattering of light from this damage site (or absorption by the plasma), which

M 7251

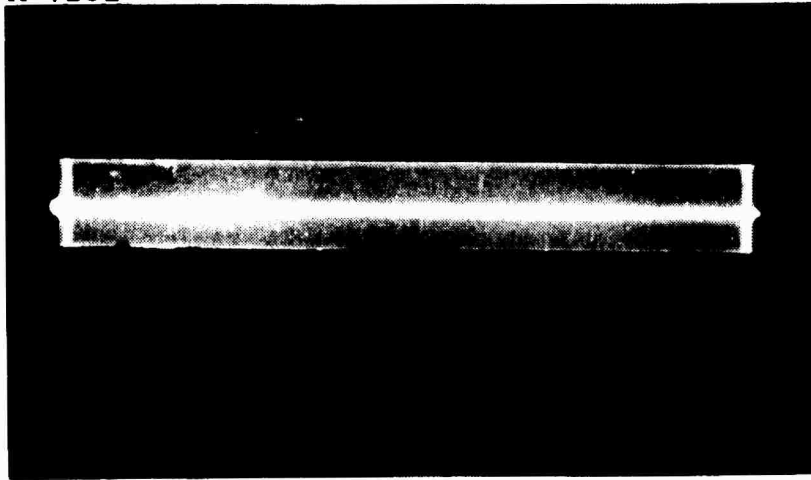

(a) No internal damage.

M 7252

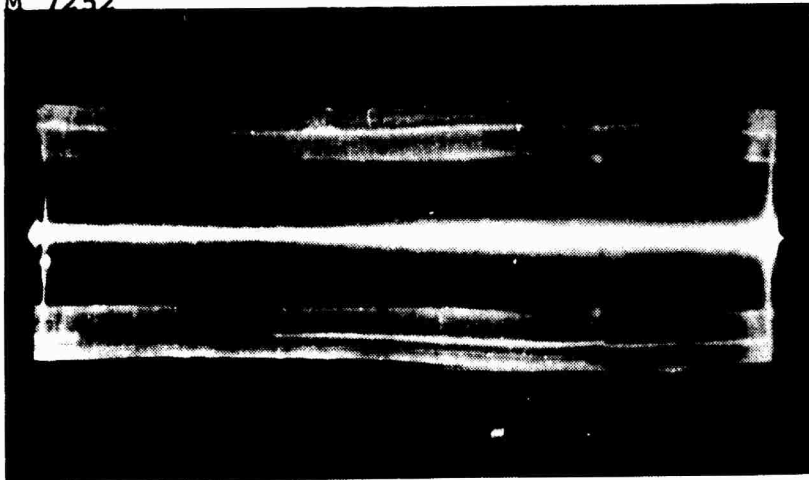

(b) Internal damage plus flaring of beam.

Fig. 4. Photographs of ruby samples while being subjected to laser radiation. Note surface plasma formation. The light is traveling from left to right.



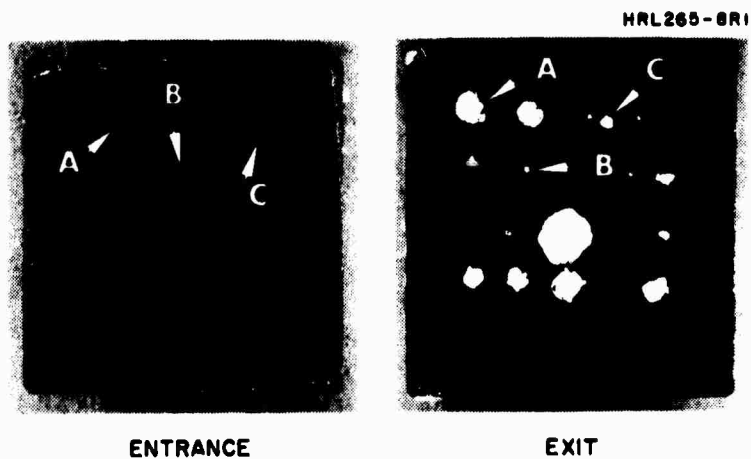


Fig. 5. Exit (right) and entrance (left) surfaces of damaged ruby sample (1/4 in. square) after a number of shots. The regions A,B, and C are relevant to the discussion in the text.

could result in a much lower power density in the interior of the sample than expected. It has been observed that once this entrance surface damage has been formed it is very difficult, if not impossible, to create bulk damage with subsequent shots in the same place. For example, when the same region of the sample is repeatedly irradiated with the laser, each time with increasing power, the bulk damage threshold often cannot be reached; however, the damage on both surfaces generally increases from shot to shot. The problem of surface damage varies considerably from sample to sample and from place to place in a given sample. No substantial difference in this behavior is seen when the surfaces are cleaned with hot nitric acid and rinsed thoroughly with deionized water. (Generally all surfaces are cleaned with ethyl alcohol.)

The photographs in Fig. 5 are presented so that there is a spatial correspondence between the entrance and exit surfaces. As an example of the variation in results for different parts of the sample, let us compare the different regions marked on the photographs. In region A, for example, both entrance and exit damage are observed in a location subjected to several shots from the laser. This region was not damaged internally, even though the power incident on the sample far exceeded that for which internal damage was created in other regions (e.g., region B). Region B is one in which both internal damage and exit surface damage were generated (in this case with one shot), with barely noticeable entrance surface damage. Region C shows a location subjected to a single shot of less than half the total energy as in B. In this case no internal damage was formed but the exit crater is considerably larger than that seen in B. Figure 6 shows entrance and exit surfaces of another sample, where we again see the qualitative features of the different kinds of damage formed. Note the general anticorrelation between the extent of entrance and exit damage as exemplified in Regions A and B. In one case (B) we see exit damage with little or no entrance damage, and in the other we see just the opposite. Next let us compare the entrance and exit surface damage at somewhat higher magnification. Figure 7 shows a magnified view of one of the damage sites seen on the entrance surface of the sample shown in Fig. 6. Here we wish to point out the crazed appearance of the surface. There appears to be a general direction to the crazing on the surface that is the same for all the damage sites examined on that crystal. Other crystals also show this type of linear crazing, but it is not seen on all the samples examined. Figure 8 shows magnified views

HRL265-9RI



Fig. 6. Exit (right) and entrance (left) surfaces of damaged ruby sample ( $3/8$  in. square). The regions A and B are discussed in the text.

HRL 265-4


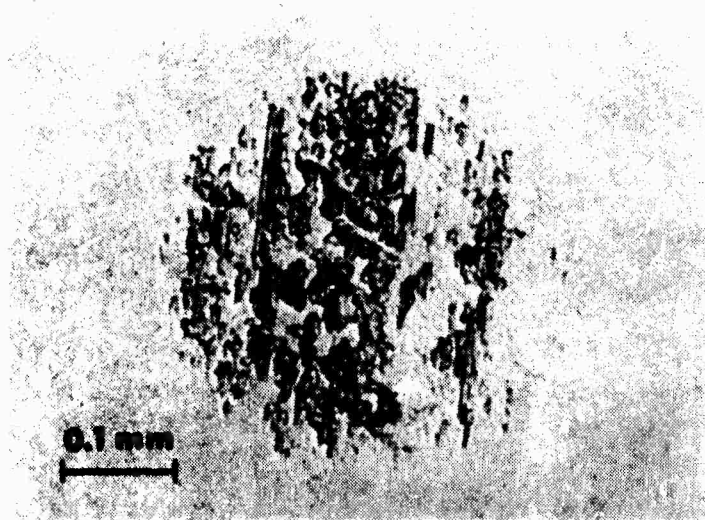



Fig. 7. Magnified view of entrance surface damage such as seen in Figs. 5 and 6.

HRL 265-6

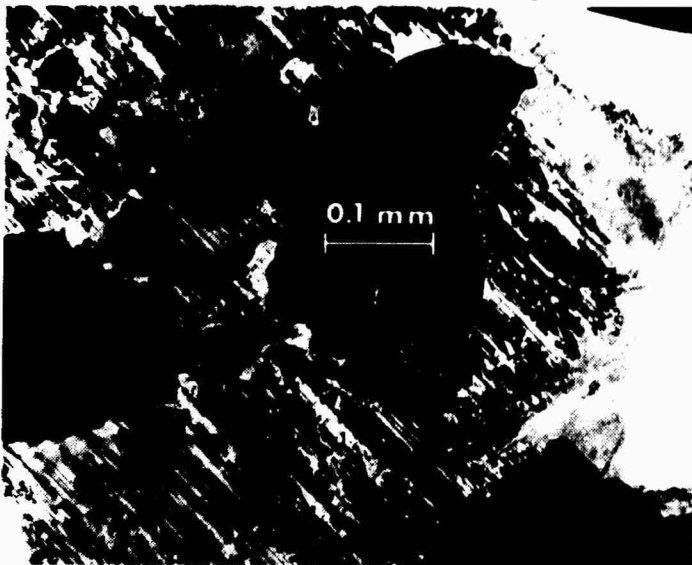


(a) End view.

HRL 265-3

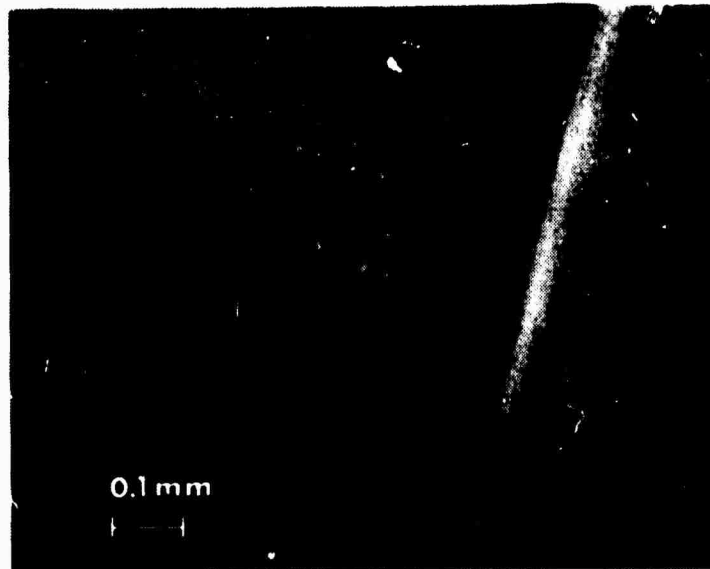

(b) Side view.

Fig. 8. Photomicrographs of exit surface damage pits and crazing.

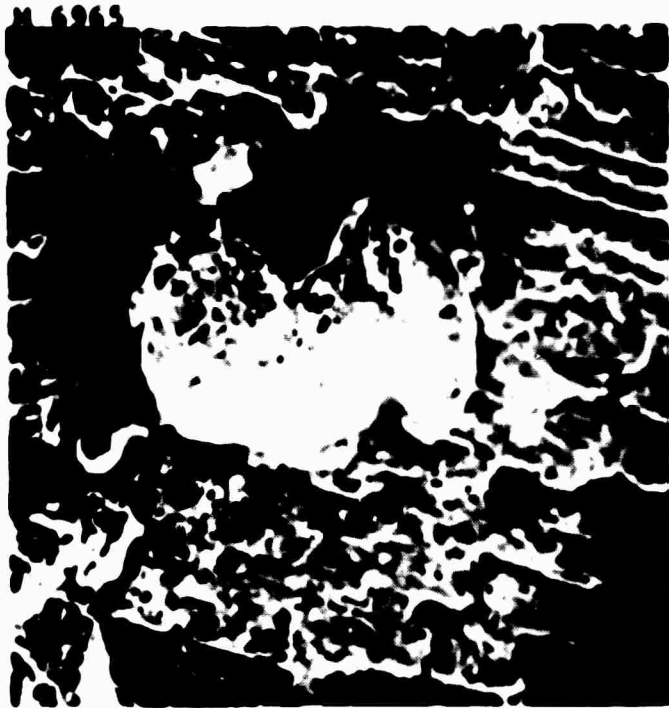

**Fig. 9. Scanning electron micrograph of exit surface damage in ruby showing crazed region and surface pitting. Marker length is 15  $\mu$ m.**

of exit surface damage. In the last report we presented a number of pictures of exit surface damage taken with a scanning electron microscope. We reproduce one of those at this time in Fig. 9 for the purposes of the present discussion. Note that the exit surface damage consists of pitting or crater formation, as well as the crazing similar to that seen on the entrance surface.

## 2. Bulk Damage

During these studies we have noticed a difference between the qualitative features of the bulk damage in ruby, compared with sapphire. This is illustrated in Figs. 10 and 11. In Fig. 10 we see some typical damage tracks seen in a ruby sample. These tracks appear to be a series of bubbles or small fractured regions of variable spacing; they are more densely packed at the beginning of the track and spread out toward the end, so that in some cases there is an appreciable gap between damage sites in a given damage track. The beginning of the track generally shows a more densely damaged region that is usually much wider than the rest of the track. In contrast, the bulk damage in sapphire appears to be qualitatively different. In Fig. 11 we see an example of typical damage tracks observed in sapphire. These are generally more continuous (fewer interrupted) than those seen in ruby, and often contain a "hollow" core with fractured regions at the periphery (see a in Fig. 11).

In this particular sample there were a few irregular tracks such as that shown in b of Fig. 11). It is curious to note that these tracks occurred when there was appreciable temporal modulation in the laser pulse. When these measurements were made there was an unusually high percentage of modulated shots. It was noted that the irregular damage occurred only on those shots when the pulse was modulated (about six times). We offer no interpretation of this observation, but merely point it out as a curious occurrence.

This section may be summarized with the following statements concerning the qualitative features of the damage in ruby and sapphire.

There are three distinctly different types of damage: bulk, entrance surface, and exit surface damage. The surface damage appears to be similar in both ruby and sapphire while the bulk damage differs as described above.

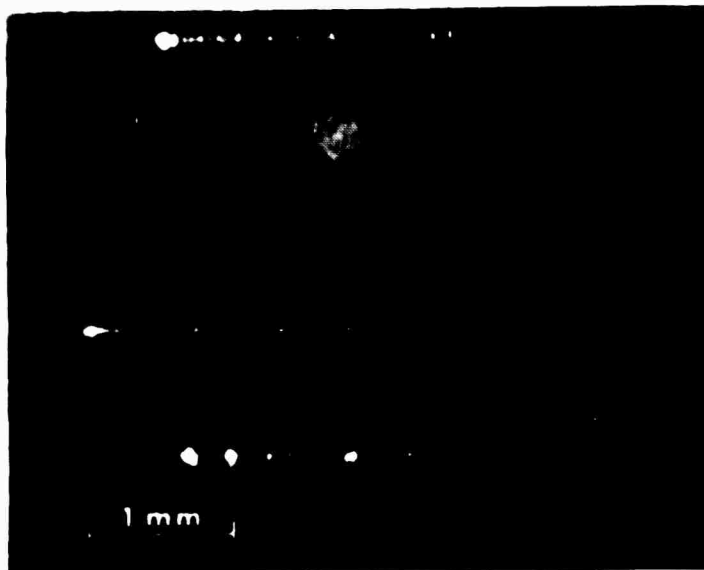


Fig. 10. Photomicrograph of damage tracks in ruby (see text for discussion).

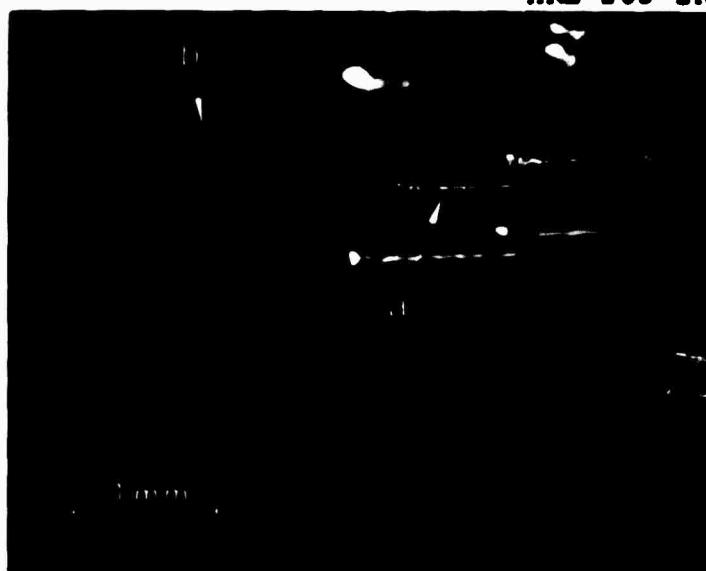


Fig. 11. Photomicrograph of damage tracks in sapphire (see text for discussion).



Entrance and exit surface damage are similar in two respects and differ in a third. They are similar in that plasmas occur at both surfaces and both show some crazing at the damage site. They differ in that a fracture crater occurs on the exit and not on the entrance surface. We suspect that the crazing is connected with and perhaps caused by the plasma that is seen at both surfaces, whereas the crater, which is unique to the exit surface, is generated by a phenomenon that takes place in the bulk of the material and manifests itself at the surface.

The threshold for exit surface damage is about an order of magnitude lower than that for bulk damage. It is more difficult to make a definitive statement concerning the relative thresholds for entrance surface damage and internal damage. The ease of plasma formation at the entrance appears to be a function of undetermined surface parameters, the most likely of which are adsorbed substances and surface finish.\* Therefore, the state of the entrance surface definitely determines what occurs inside the crystal and at the exit surface. In the extreme case all of the light could be dissipated in the entrance plasma.

Finally, let us assume that a hypothetical sample is subjected to a series of shots with increasing energy, each time striking a different spot, and assume that the power density is uniform over the length of the sample. We will first observe exit surface damage at some threshold. As the energy is increased, the extent of the exit surface damage will increase to give a larger crater than on the previous shot. At an order of magnitude higher input we reach the threshold for bulk damage, at which point a short damage track will appear; at the same time, we will probably observe a decrease in the size of the exit pit relative to what it was just below bulk damage threshold. As we increase the energy further we will generally observe more extensive internal damage and perhaps begin to see some entrance surface damage, depending on the condition of the entrance surface. At still higher incident energy the extent of entrance surface damage (or absorption by the plasma) can be so great that it precludes the formation of bulk damage simply because not enough light gets inside to cause damage.

---

\*It is definitely known that a substantial plasma will form on a dirty entrance surface. In addition, in our limited observations it appears that those crystals with more surface scratches are more easily damaged at the entrance surface.

## E. Damage Threshold Experiments

In this section we present the results of damage threshold experiments for internal damage in a number of different materials from various sources. In all the cases presented the data represent a large number of shots for a given sample. There was a large amount of scatter in the data, as mentioned earlier; we believe this results in part from the varying amount of plasma formed at the entrance surface. It is also reasonable to believe that there is an intrinsic variation in damage threshold from place to place in the same sample. As a result, there is a range of incident energies over which one may or may not see internal damage, depending on the particular location in the crystal. For example, at a particular location in the sample no damage is seen at a given incident energy, while extensive damage may be seen in another part of the sample for a lower energy in another shot. The data presented in Fig. 12 reflect this fact. The dashed line corresponds to a range of power densities where damage was not observed at some locations in a given sample and is terminated on the high end by the highest power for which internal damage was not created. The solid line corresponds to input energies where damage was observed at some locations in the same sample and is terminated on the low end by the smallest input energy for which damage was observed. For example, let us examine the data presented for Cz Ruby L104 in Fig. 12. The dashed line shows that certain regions of the sample were subjected to power densities up to  $7.1 \text{ GW/cm}^2$  without damage. The solid line shows that damage was observed in some other parts of the sample at input power densities as low as  $6.3 \text{ GW/cm}^2$ . Thus, the amount of overlap gives a measure of the definability of damage threshold for a given sample.

The power densities in Fig. 12 are calculated power densities at the beam waist. Mode propagation equations described previously were used to compute beam radius and divergence at various locations. The energy incident on the focusing lens first is measured by photodiode No. 2 (Fig. 1). This is converted to power by dividing by the appropriate pulse width (FWHM) as determined by the Tektronix 519 oscillograms. The power density at the lens is computed by dividing this power by the area of the beam at the lens. This gives a spatial average for the power density or energy density. The energy density at the peak of the gaussian

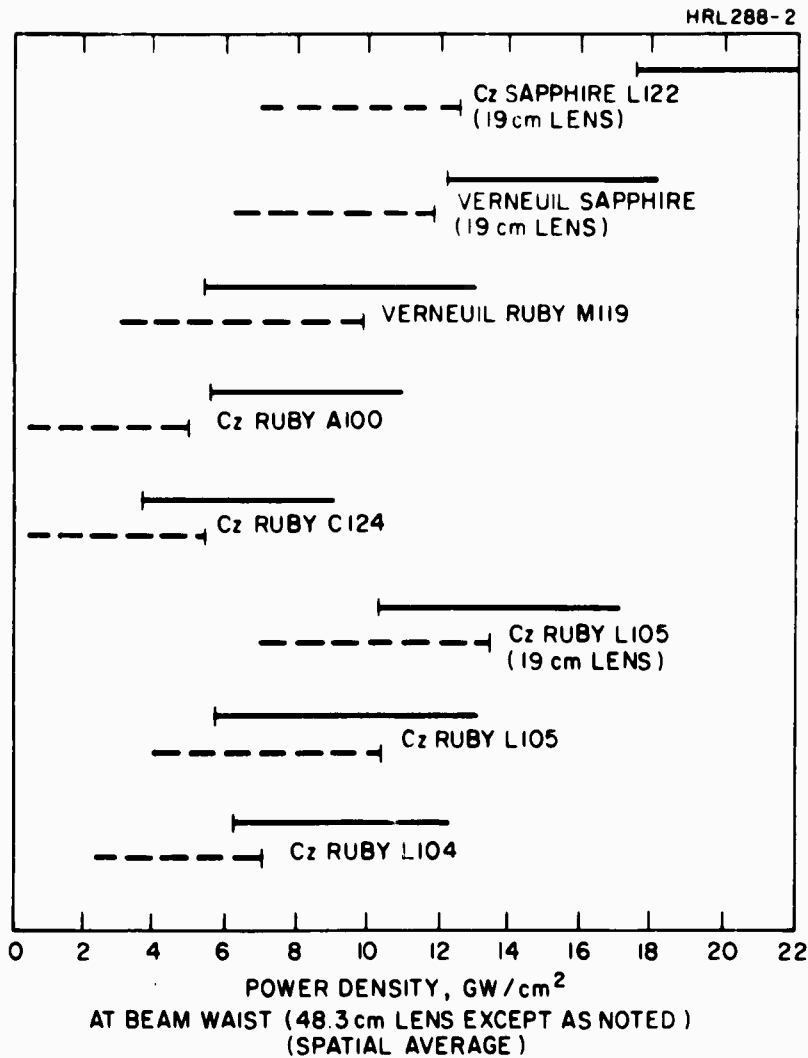


Fig. 12.

Bulk damage thresholds for a number of ruby and sapphire samples. The power density and energy density scales are spatial averages. The power and energy densities at the peak of the gaussian distribution are twice the spatial averages (see text). The dashed line corresponds to power where damage was not observed; the solid line to powers where damage was observed for a number of shots in different regions of the same sample.

Sample sources:

A100 - Airtron

L104, L105, L122 - Union Carbide

C124 - Crystal Optics

M118, M119 - Meller.

distribution is twice the spatial average.\* The power density at the focus of the lens is obtained by computing the beam size at the focus.

We wish to emphasize that these power and energy densities are based on the following assumptions: (1) The spatial profile of the output is gaussian with a 1 mm radius (1/e radius for the electric field.) (2) the spreading of the beam is by diffraction only, and the beam suffers no distortion, focusing, or defocusing in passing through the ruby amplifier. (3) The diffraction limited spot size is reached at the focal plane of the focusing lens. The degree to which these assumptions reflect the reality of the physical situation can only be estimated at present, pending further measurements. Measurements of the near field spot size at the oscillator output mirror give a 1 mm radius for the 1/e points of the electric field (assuming a gaussian distribution). This was done both by photographing a pair of spots on a ground glass screen with a known attenuation difference and by measuring the sizes of burn patterns on Polaroid film, with the relative energies of successive shots known. The measurements by both techniques agree to better than 15%. Measurements of the far-field divergence of the oscillator give values that are higher than that expected for a gaussian, although the measurements are not highly accurate. We obtain  $0.6 \pm 0.1$  mrad (full angle) from relative spot size measurements in the focal plane of the 1 m focal length camera.<sup>†</sup> The calculated beam divergence gives 0.44 mrad ( $\theta \approx (2\lambda)/(\pi\omega_0)$ ; full angle);

\*The gaussian beam radius  $\omega$  is defined as the radius for which the electric field reaches 1/e of its peak value. This is the radius for which the intensity or the energy density reaches  $1/e^2$  of its peak value. If we define a beam area  $A = \pi\omega^2$  and divide this into the total energy  $E_{tot}$ , we have a kind of average energy density. It is easy to show that the energy density at the peak of the gaussian distribution is  $2E_{tot}/\pi\omega^2$ . In most of the reports in the literature the power densities or energy densities refer to a kind of average. That is, the total energy is divided by the "beam size" determined by some means or other. This method is convenient when the spatial power distribution is not known.

<sup>†</sup>It is easy to show that the 1/e diameter for the intensity is  $D_I = \sqrt{d_1^2 - d_2^2 / \ln \alpha}$ , where  $d_1$  and  $d_2$  are the measured spot diameters and  $\alpha$  is the ratio of the intensities (for density 0.6,  $\alpha = 4$ ). The 1/e diameter for the field is  $D_E = \sqrt{2} D_I$ .

this is appreciably lower than that observed but is almost within the uncertainty of measurement. Even though we are well below the saturation flux for the amplifier ( $4\text{J}/\text{cm}^2$  compared with  $15\text{J}/\text{cm}^2$ ), the uncertainty in the effect on the beam properties of the amplifier is probably the largest and most difficult to estimate. Characterization of the beam after passing through the amplifier will be carried out soon.

#### F. Dependence of Damage Threshold on Added $\text{TiO}_2$

Recent work of Nath and Walda<sup>1</sup> reported a striking increase (40x) in the damage threshold in sapphire when small amounts (20 to 100 ppm) of  $\text{TiO}_2$  were added. We decided to check these results and extend them to ruby as well. We purchased Verneuil ruby and sapphire samples from the same source used by the above workers (Djeva in Switzerland via Adolf Meller Co.), both undoped and doped with nominally 30 ppm  $\text{TiO}_2$ . The thresholds for internal damage were measured, and the results were found to be essentially opposite those reported previously. Table II shows the results of these measurements. The numbers in the table are given in pairs. As discussed in connection with the data in Fig. 12, the numbers reflect the variation of threshold from place to place in the sample. Of the two numbers quoted, that on the left is the highest value for which damage was not observed in the sample, and that on the right is the lowest value for which damage was found in the same sample. We see from Table II that the thresholds for the titanium doped samples are at least an order of magnitude lower\* than those for undoped samples. The reason for this discrepancy with the results of Nath and Walda is not known. In addition, contrary to the results of Nath and Walda, we found that the ultraviolet absorption edge for the  $\text{TiO}_2$  doped samples occurred at a shorter wavelength than that for the undoped sapphire (2600 versus 2300 Å). This is shown in Fig. 13.

---

<sup>1</sup>G. Nath and G. Walda, "Strong Radiation of Laser Produced Damage in Sapphire and Ruby by Doping with  $\text{TiO}_2$ ," Z. Naturforsch. 23a, 624-625 (1968).

\*These titanium doped samples are examples of ruby and sapphire for which the bulk damage threshold is so low that surface damage does not form.

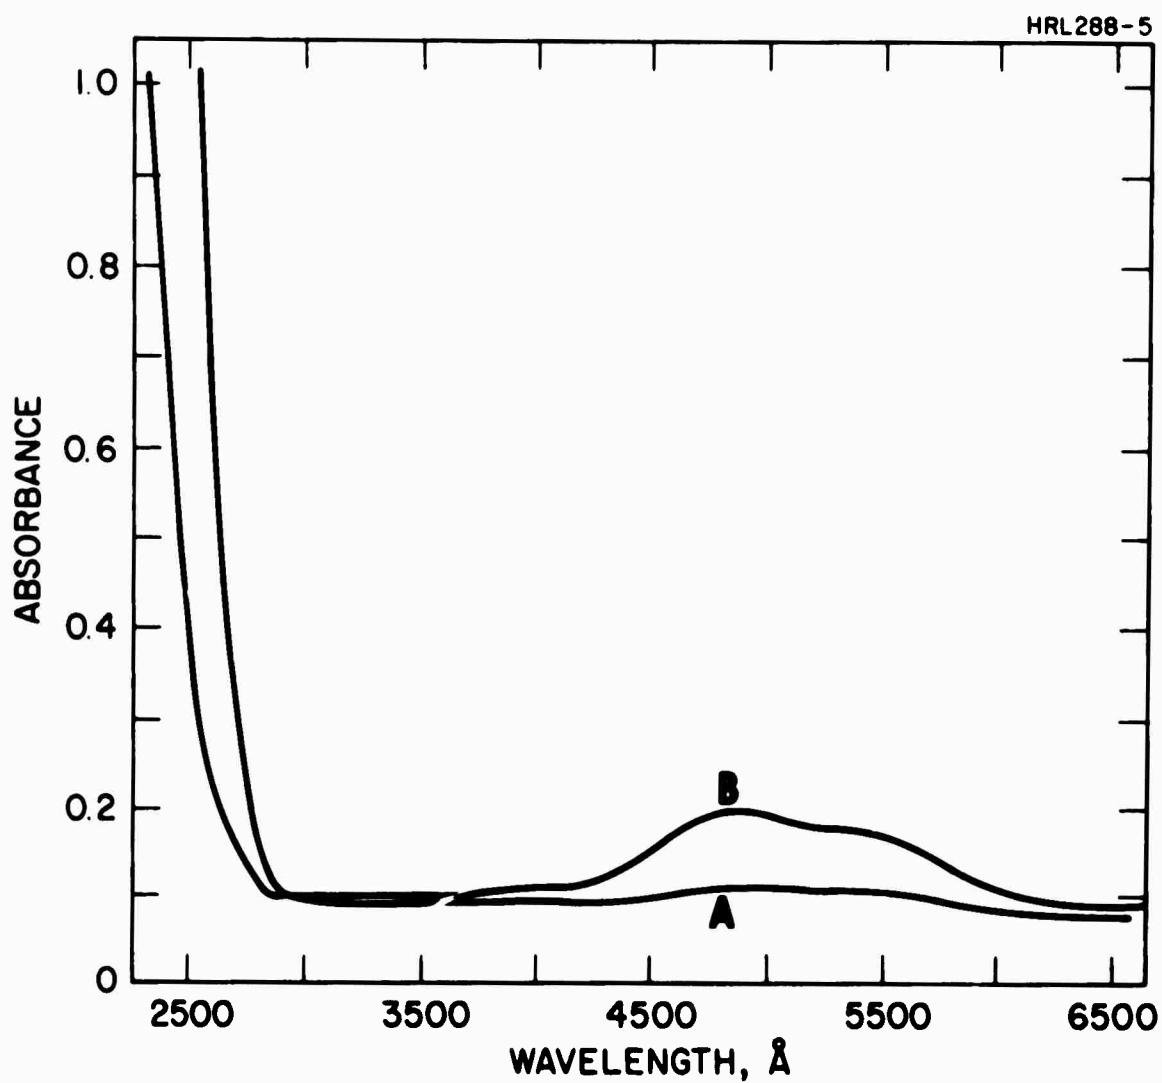


Fig. 13. Absorption spectra of Verneuil sapphire whose thresholds are reported in Table II. (a) Undoped. (b) 30 ppm  $\text{TiO}_2$ . These spectra were taken with a Cary 14 spectrophotometer using air as a reference.

TABLE II

Effect of  $\text{TiO}_2$  Doping on Damage Threshold

	Power Density for Internal Damage, $\text{GW}/\text{cm}^2$	
	Without $\text{TiO}_2$	With 30 ppm $\text{TiO}_2$
Verneuil Ruby	5.4, 9.9	0.94, 0.70
Verneuil Sapphire	12.1, 9.4	0.36, 0.52

T40

Because of these discrepancies it is reasonable to suspect that we may in fact have different material from that studied by Nath and Walda. The future course of this work is at present uncertain.

#### G. Optical Pumping Experiments

During this reporting period we have carried out a few experiments in which we optically pumped the samples while subjecting them to the laser radiation. Figure 14 shows the apparatus used for optically pumping. It was designed so that the sample could be examined closely between shots without the need for removal from the apparatus. The experiments were carried out on two ruby samples and one sapphire sample.

The samples were pumped with a power supply similar to that used for pumping the amplifier flash lamp. In these experiments we pumped at two different levels (1200 J and 3700 J) into the flash lamp (model FX60 by E.G.&G.). As in the previous experiments we fired a number of shots (generally 10 to 20) at each pumping level for a given sample.

The results of the threshold versus pumping experiments are shown in Fig. 15. Here the results are depicted in a manner similar to that of Fig. 12, where the dashed line refers to the powers where no damage was seen in some parts of the crystal and the solid line to powers where damage was seen in other parts. The scatter in the data is relatively high, but nevertheless we can confidently say that there is no appreciable lowering of the threshold with optical pumping and, if anything, there may be a slight increase.

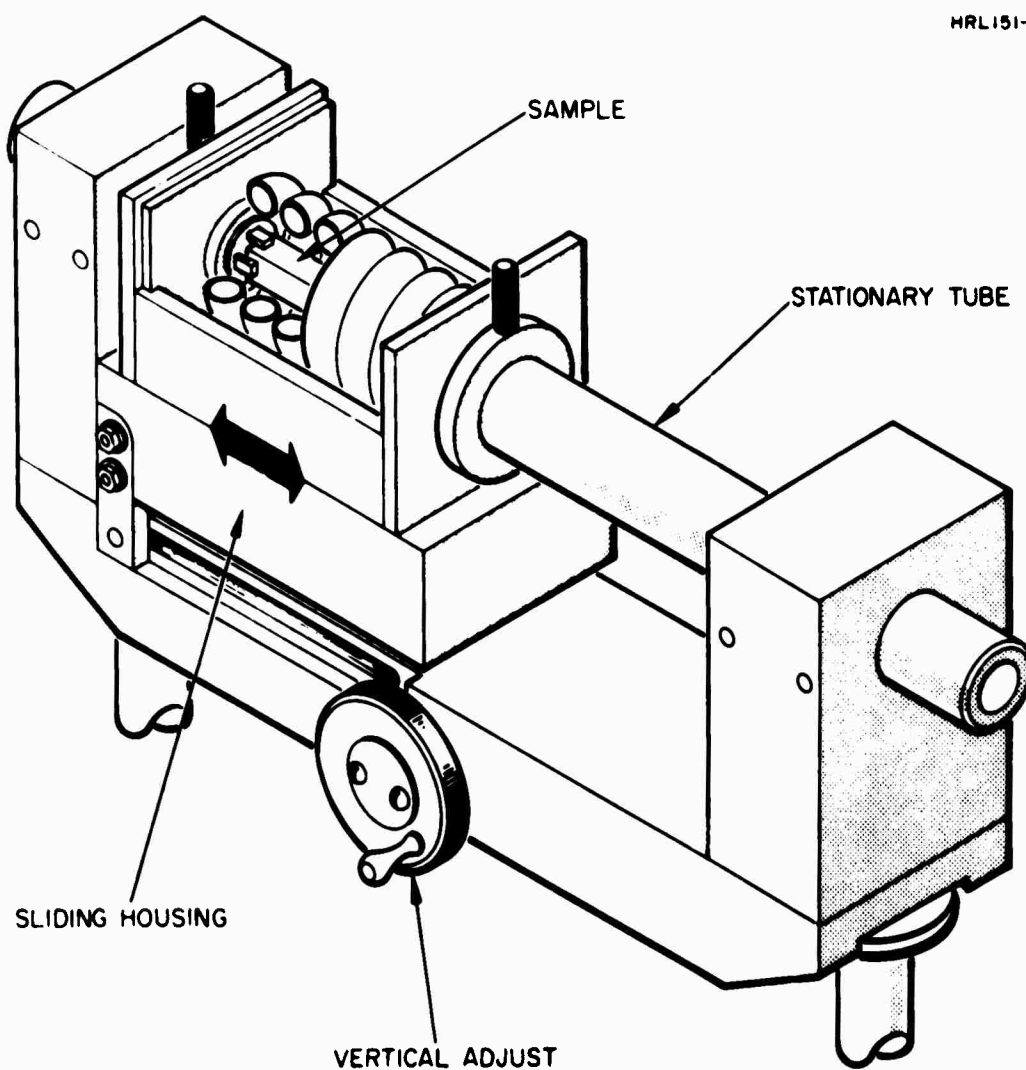


Fig. 14. Apparatus used for optical pumping experiments.



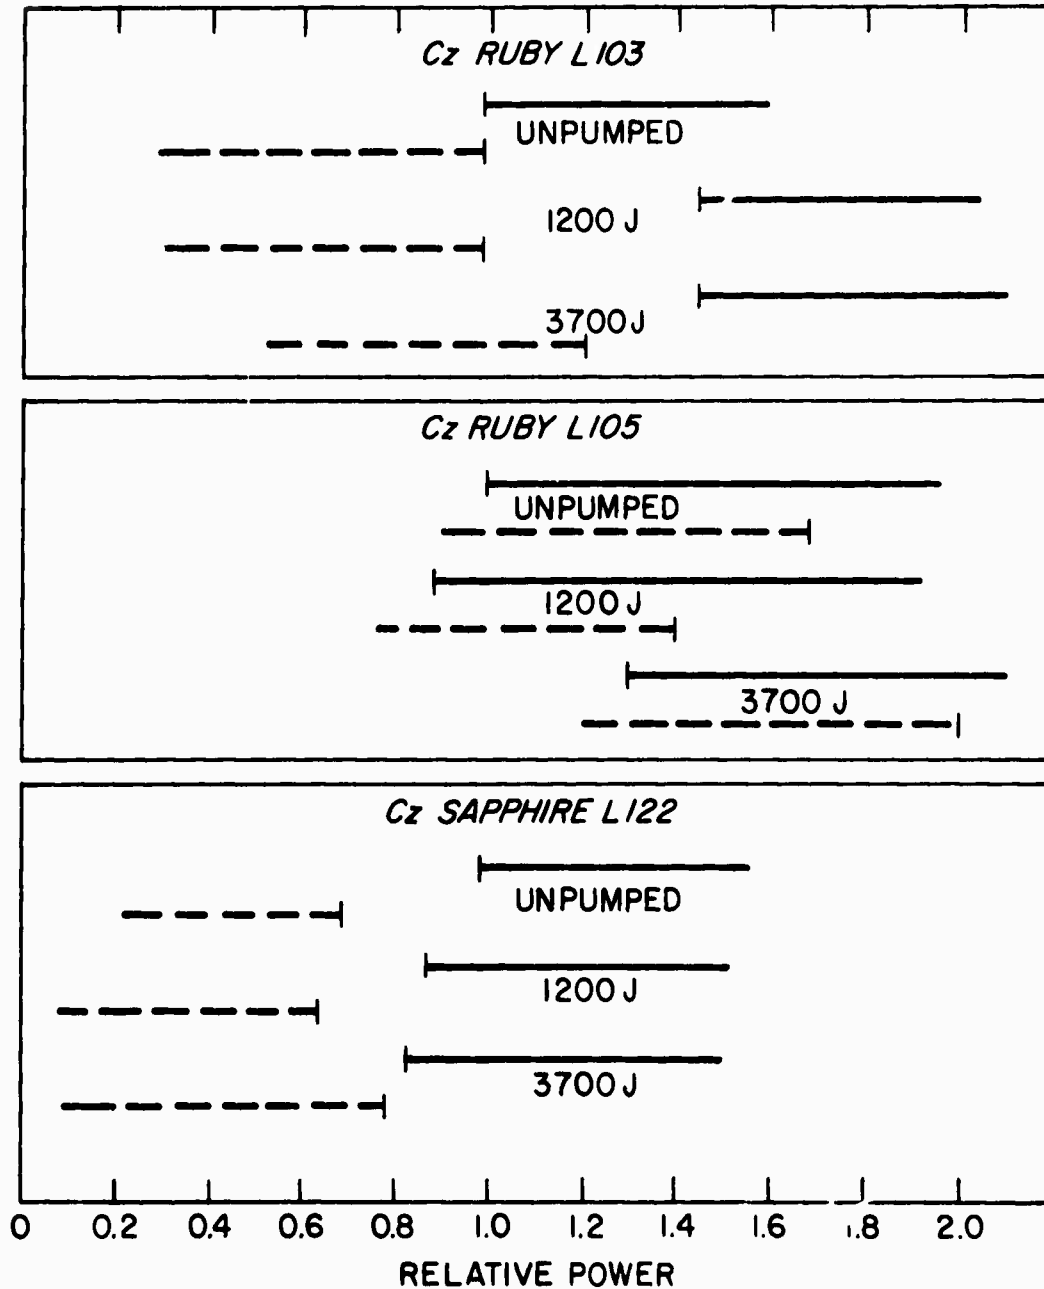


Fig. 15. Relative bulk damage threshold as a function of optical pumping for different samples. The thresholds are normalized to unity for each sample (unpumped). Dashed line - no damage; solid line - damage.

One reason for the scatter in this case is the use of a shorter focal length lens than has been generally used (19 cm compared with 48 cm). We used this lens because the output from our system was somewhat lower than previously and we were not quite able to reach damage threshold with the long focal length lens. A more extensive plasma was formed at the entrance surface at times when the 19 cm lens was used, and an appreciable fraction of the light undoubtedly was absorbed by the plasma. The experiments will be repeated with the sample in a different position so that this will not occur as readily.

We observed another interesting phenomenon in these pumping experiments related to the location of the damage in the crystal as a function of pumping. In ruby that is not externally pumped, we see damage tracks whose beginning is usually uniquely located in the sample. That is, for a number of shots at different powers we find that the damage tracks begin at roughly the same distance from the entrance surface. The length of a given track generally will be longer for higher power.

When the ruby samples are optically pumped, we see damage tracks that begin at an appreciably different location "downstream" from the tracks for the unpumped sample. Harder pumping shifts the tracks even more. This phenomenon is reversible; results for a sequence of nonpumping, pumping, nonpumping, pumping are reproducible.

The results of these experiments are shown in Fig. 16, where the location of the beginning of the damage track is plotted as a function of energy discharged into the flash lamp. The lengths of the bars on the plot reflect the variation in position from shot to shot of the beginning of the damage track.

This effect of apparent defocusing of the light cannot be explained as a sort of thermal focusing due to the optical pumping; it is much too large for that. For example, if we were to assume that the ruby has somehow become a negative lens, we might ask what the effective focal length would be. Taking into account the distance of the entrance surface of the ruby from the lens and assuming that the shift in the location of the damage track corresponds to a shift in focus, we compute that the ruby would have to act as a negative lens of  $\sim 20$  cm focal length, which corresponds to a radius of curvature of the end of the rod of  $\sim 7$  cm.

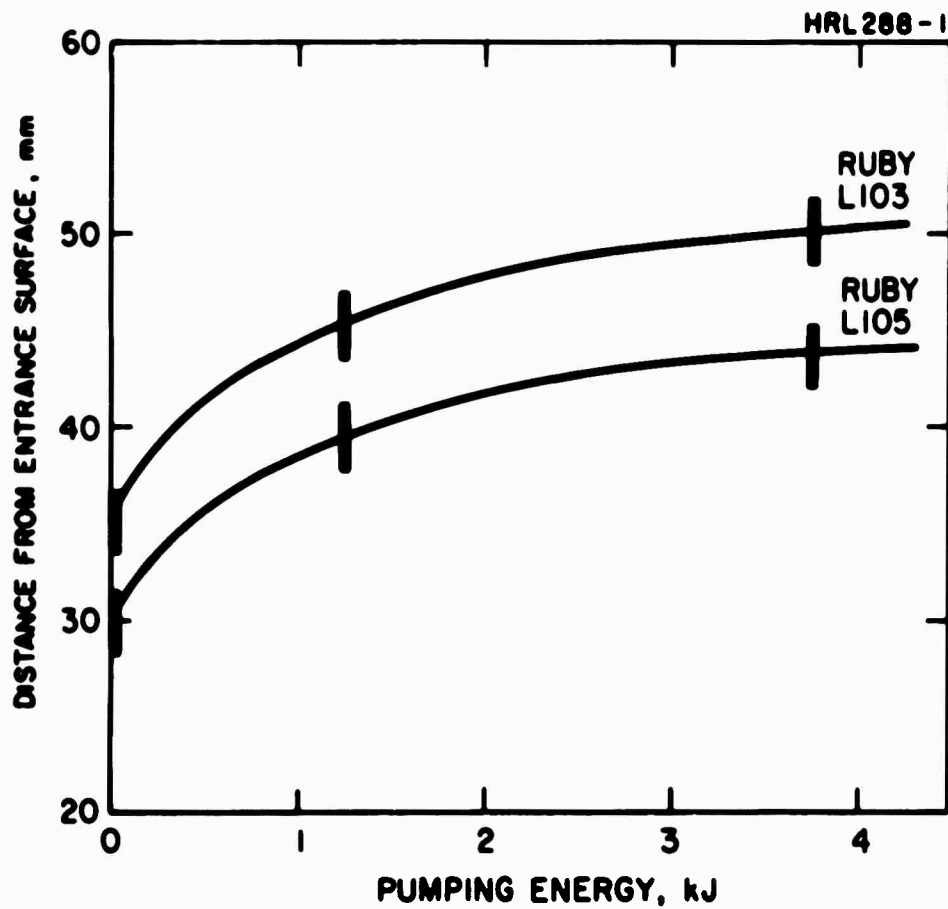


Fig. 16. Location of beginning of damage tracks from entrance surface versus optical pumping energy for ruby samples. L103 - 0.03% Cr<sup>3+</sup>, L105 - 0.05% Cr<sup>3+</sup>.

Alternatively, we can compute the apparent change in refractive index with pumping to account for the shift in the position of the damage track. The relative shift in the distance from the entrance surface to the focus is directly proportional to the relative change in refractive index. This then corresponds to an apparent index change of 40 to 50%, a very large effect!

It is difficult to account for this effect by postulating any change in the linear refractive index. A decrease in nonlinear index that somehow depends on the degree of optical pumping is a possible explanation, but this should result in a higher damage threshold for pumping than for nonpumping. This may be the case, but there is too much scatter in the data to confirm this (Fig. 15). We also mentioned that in the pumping experiments there was a substantial amount of plasma formation at the entrance surface. It is conceivable that optical pumping of the surface plasma could lead to some defocusing effect. It is clear that more experiments in this area are needed, especially with regard to the relative damage thresholds.

A correlation for sapphire similar to those seen for ruby in Fig. 16 does not exist. The location of the beginning of the damage tracks in unpumped sapphire varies over a much wider range, depending on the incident energy from the laser, and any effect of optical pumping is obscured by this variation.

When the incident laser power is close to threshold the damage is found farther "downstream"; as the incident energy increases, the location of the beginning of the track moves "upstream" toward the source. This is illustrated in Fig. 17, where we plot the distance of the beginning of the damage tracks from the entrance surface versus laser power incident on the focusing lens.

#### H. Plans for Next Period

One of the first tasks to carry out will be the measurement of the beam characteristics after the amplifier. Dependence of damage threshold on the size of the focal spot will be studied, and the optical pumping experiments will be repeated in an attempt to obtain better reproducibility in the data. The evolution in time of the damage track will be studied using an image converter camera.

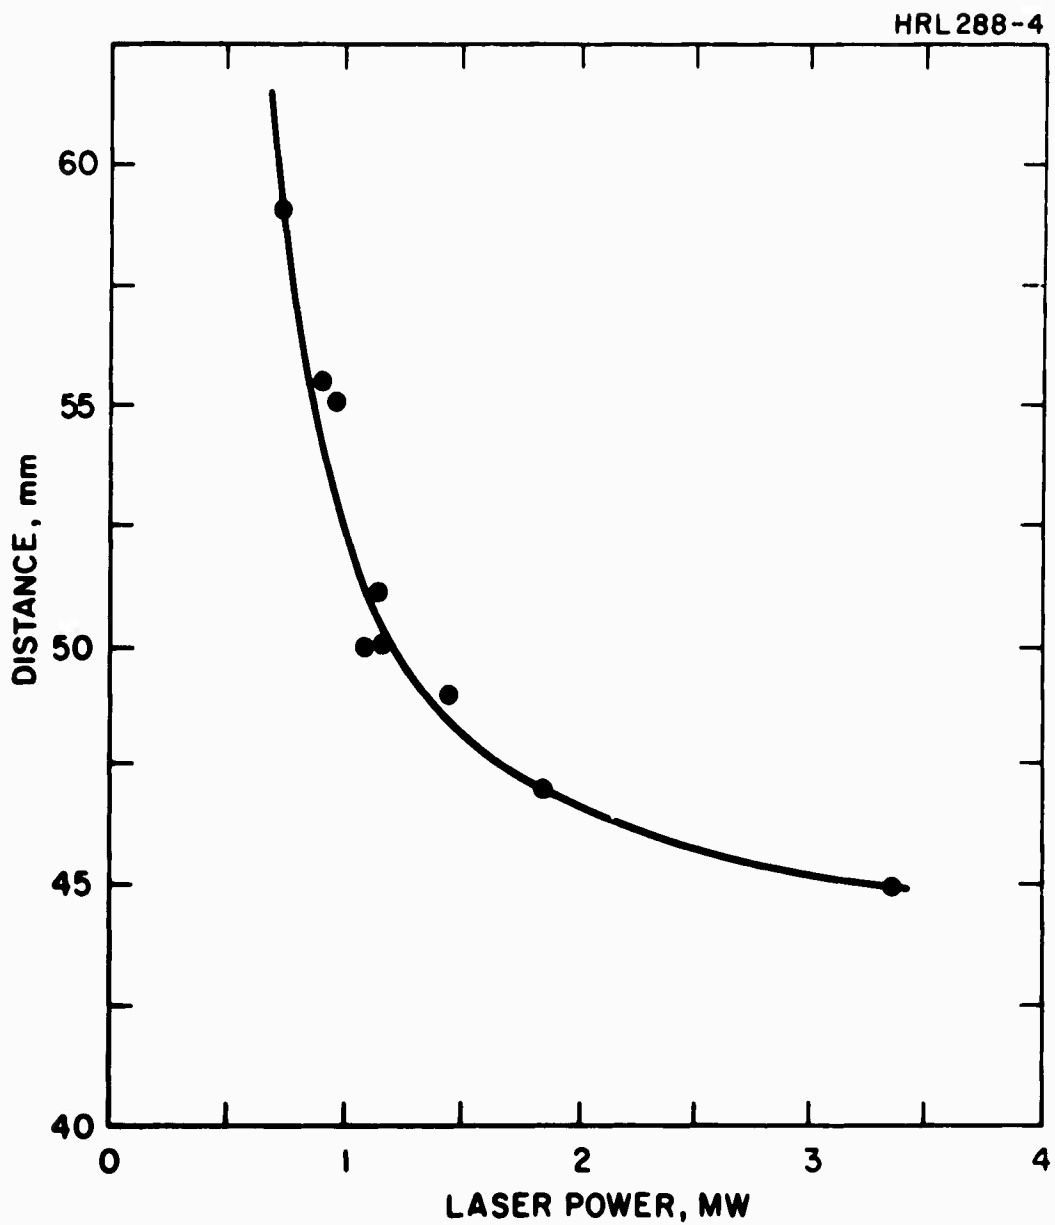


Fig. 17. Location of beginning of damage tracks from entrance surface versus laser power incident on 19 cm lens for Cz sapphire sample L122.

**BLANK PAGE**

## II. THEORETICAL STUDIES ON OPTICAL DAMAGE

### A. Introduction

In the theoretical studies conducted for this project we have first established a broad outline or "scenario" of optical damage as it is caused in the best quality ruby and sapphire by laser pulses of order 20 nsec duration and shorter. This general examination then led us to a concentrated study of a previously unexplored class of mechanisms which we thought might play a central role in the breakdown of sapphire and ruby. These mechanisms involved the ability of a relatively low-density ( $\sim 10^{16} \text{ cm}^{-3}$ ) of cold photoexcited conduction electrons (1) to transfer energy rapidly and efficiently from the optical beam to the lattice and (2) to accelerate the excitation of even more conduction electrons, thus aiding further in the energy transfer of (1). In subsection B we review the general damage picture as we see it, and then in subsection C the results of our studies of photoelectron dynamics in strong optical fields are presented. For details pertinent to these sections, the reader will be referred to a paper which is reproduced here as an Appendix.

### B. A Proposed General Outline of the Process of Optical Damage in Sapphire and Ruby

We have found it useful to view in five stages the over-all damage process in ruby or sapphire (often referred to as "the crystal"). These stages are as follows:

(1) Before actual physical rupture of the lattice occurs, a certain spatial and temporal distribution of optical fields that is able to initiate the damage process is reached or exceeded in the crystal. A comprehensive description of the threshold beam conditions for short pulses is far from being complete, being dependent on the outcome of researches on all the phases of the damage process. Roughly speaking, it is believed that if the beam can deposit from  $10^2$  to  $10^3 \text{ J/cm}^3$  in a small region of the crystal in less time than it takes heat to diffuse out of the region, then a rupturing shock wave will develop. As a working rule of thumb, a pulse of duration  $10^{-8}$  to  $10^{-10}$  sec and of order  $10^{-2} \text{ cm}$  in diameter cannot exceed several times  $10^{10} \text{ W/cm}^2$  peak intensity without initiating damage in ruby or sapphire. However, several remarks are in order.

First, the visual appearance of damage tracks suggests that self-focusing of the optical beam is instrumental in increasing the beam intensities into the damaging regime. This is not definitely established and is under investigation in this project and elsewhere. However, if self-focusing is aiding in the initiation of damage, then the above numbers have grown out of some probably incorrect interpretations of data and may require modification. To better establish the degree of self-focusing, a definitive measurement of the "fast-responding" part of the nonlinear index of sapphire and ruby would be helpful. Early in this project, we examined the possibility that transient electrostriction could produce self-focusing at observed damage power thresholds and found it to be extremely remote. Whether or not self-focusing is occurring from other mechanisms we view the subsequent stages of damage roughly as follows.

(2) The intense optical beam next promotes a number density of order  $10^{16}$  electrons/cc from impurity levels into the conduction band. This can happen by the direct or "linear" photoexcitation process observed by Hochuli (Ref. [5] of the Appendix) at low optical intensities ( $\sim 5 \text{ W/cm}^2$ ). More likely, this excitation is produced by complex multistage, or even "bootstrap" avalanche, processes that resulted in the highly nonlinear photoconductivity observed by Belikova, et al. (Refs. [7,8] of Appendix), at high optical intensities ( $\sim 10^{10} \text{ W/cm}^2$ ). The studies of some new processes of the latter kind made under this project are discussed in subsection C.

(3) The strong optical field seen by electrons reaching the conduction band imparts to them some added random motion (heating) and some coherent oscillatory motion. Previous workers have concentrated on the heating effect (Refs. [1-4] of Appendix), supposing that the electrons might gain enough random energy to ionize the lattice, promoting other electrons across the band gap ( $\sim 8 \text{ eV}$ ) in an avalanche process. We have examined this possibility in detail starting, as did previous workers, from Fröhlich's well-known model for electron-lattice interactions. We found to be negligibly small the probability of an electron's gaining even one eV of random energy at nominal damage intensities ( $\sim 10^{10} \text{ W/cm}^2$ ). However, when we examined the effects of the low-energy coherent motion ( $\sim 10^{-3} \text{ eV}$ ) of a "cold" electron in the intense field superposed on the small thermal motions (appropriate to a temperature not much above the ambient lattice temperature), we found a potentially damaging situation. These oscillating electrons spontaneously



radiate longitudinal optical (LO) phonons at a significant rate, much as an electromagnetic antenna radiates photons. (We also calculated the rate of stimulated emission of phonons by the oscillating electrons but found this to be negligible.) Our efforts in assessing this phonon radiation rate are described in subsection C.

(4) The LO phonons radiated by the conduction electrons have a nearly vanishing group velocity and do not carry their energy out of the region of the beam rapidly. Although direct measurements of the lifetimes of the most important phonons (which do not have a small wavevector) are unavailable, we believe that they decay rapidly into acoustic phonons in a time short compared to laser pulse lengths, in essence depositing a certain thermal energy very close to the electrons that radiated them. This means that there is an equivalent heat source formed in the irradiated parts of the crystal.

(5) In the final stage of damage, the large random acoustic (heat) energy generated from the LO phonons forms shock waves which then rupture the crystal, generally some time after the optical pulse has passed. It is not beyond the theory of shock waves in solids to estimate the strains developed as they propagate away from the heated region. However, it would be a formidable computing task and we have not attempted it. Other efforts in the project have been concentrated as outlined in the following section. Before discussing these efforts, however, we might make a few critical remarks about the above review of damage.

There are various potentially damaging processes which lie outside the foregoing outlines. We have examined all of those known to us and have found them to be probably less important than those outlined, or at best only occurring in a final holocaust when they are not needed, if indeed they would still be identifiable. Among the most prominent of these are stimulated Brillouin, Rayleigh, and Raman scattering. In the first two instances, we have investigated the degree of stimulation of density waves for purely electrostrictive and for absorptive (thermal) coupling. It seems very unlikely from existing electrostrictive data that significant stimulated Brillouin waves would develop. Significant gain from absorptive coupling exists if some mechanism (such as our conduction electron mechanism) can produce optical absorption of order one  $\text{cm}^{-1}$ . But at this level of absorption, damage from other effects of the heating will certainly obscure any stimulated effects.

Raman scattering cross sections are not well known, but there has never been observed at damage the distinctive strong Stokes and anti-Stokes sidebands that accompany stimulated Raman scattering.

### C. The Role of Photoelectrons in Crystal Damage

In this project we have examined two of the many questions surrounding the roles of photoelectrons in the various stages of the damage process which we outlined in the preceding section. First, we have studied the rate at which a single conduction electron transfers energy from the optical field to the LO phonons. Second, we have estimated how the presence of conduction electrons at densities of the order of  $10^{16}/\text{cc}$  affects the rates at which electrons initially bound to impurities (dislocations, foreign ions, etc.) make transitions to higher energy impurity levels, both bound and unbound.

The first question has been answered with the most surety. Fortunately, sapphire and ruby are polar crystals, and in polar crystals the interactions of cold electrons with the LO phonons dominate their interactions with other phonons; and a particularly simple model of this interaction derived first by Fröhlich (Ref. [10] of Appendix) has proven to give remarkably accurate predictions of mobilities, effective masses, and even cyclotron level shifts in a wide variety of materials. The only parameters in this model are the static and optical dielectric constants, the LO phonon frequency (or its average), and the effective band mass of the conduction electron. Unfortunately, the last is not known for sapphire, but experience with other ionic, high band gap materials indicates it is easily within order of magnitude of the free electron mass. More fortunately, the rates we seek do not depend too strongly on the effective band mass, typically varying as its square root. A further complication is that the electron-phonon interactions in sapphire and ruby cannot be treated by quantum perturbation theory. The dimensionless perturbation expansion parameter  $\alpha$  defined by Fröhlich is roughly three in this case, and only for  $\alpha \ll 1$  is perturbation theory accurate. The author, with others, has previously developed a method for treating such cases of "intermediate coupling" (Ref. [6] of Appendix). This method is based on a minimum-variational principle. Long experience with a certain two-parameter variational function has indicated that, used in computing

the electron response in the manner prescribed in Ref. [6] of the Appendix, this function will yield an optical absorption rate for a conduction electron accurate to within  $\sim 10\%$ . The uncertainty in the band mass contributes much more uncertainty in our final results, so refinements of the variation function, or in other approximations in its use, are not warranted. The numerical details of this calculation of the optical response, and from it the phonon radiation rate, of an electron in sapphire or ruby are given in Section 4 of the paper reproduced as the Appendix.

The second question studied in this project sought to determine whether the presence of  $\sim 10^{16}$  conduction electrons/cc could significantly affect the rate in which impurity electrons made up their ladder of levels and hence contribute to the very nonlinear behavior of the dc photoconductivity observed by Belikova, et al. (Refs. [7,8] of Appendix), in what are probably the only high-intensity experiments reported to date which avoided many spurious effects of surface conductivity. The impurity level structure of sapphire and ruby is seen to be very weak but very complex from existing infrared absorption and luminescence data. Unfortunately, the densities of impurities of different types are completely unknown as is the structure of any given type. One can make crude estimates, however, with various physical models, of the transition matrix elements required in a simple Born approximation or dipole approximation treatment of optical field-electron-impurity interactions. Using what we felt were conservative guesses, we found that the impurity transition rates could be affected in an important way by the conduction electrons. This is especially true for the majority of bound-bound transitions normally not resonant with the optical beam, for these transitions become allowed when the conduction electrons can carry away the excess transition energy. Optical cross sections for such electron-enhanced transitions are found to be of the order of  $10^{-22}$  cm<sup>2</sup>. Therefore, impurity densities of order  $10^{19}$  cm<sup>-3</sup> might bring these processes into contention, if not dominance, over direct photoexcitation. The details of these calculations are given in Section 5 of the Appendix.

Many other questions surrounding the role of photoelectrons in damage have been or are currently under study (see, for example, the Appendix). However, without much more reliable and wider range of experimental data on the impurity level structure and conduction band characteristics in optical materials of interest, definitive answers cannot

be found for what causes damage, how to prevent it, and how to detect damage-prone crystals before use. Fortunately, laser sources provide an unprecedentedly powerful tool (that has as yet been little used) for studying photoconductivity, photo-Hall effect, luminescence, and other properties of very weakly photoconductive materials, such as ruby and sapphire. Progress in controlling optical damage may be anticipated from knowledge gained from such studies in the future.

Role of Photo-Electrons in Optical Damage<sup>1\*</sup>

R. W. Hellwarth

Department of Electrical Engineering  
 University of Southern California  
 Los Angeles, California 90007  
 and  
 Hughes Research Laboratories  
 Malibu, California 90265

Previous workers have discussed the possibility that electrons photo-excited into the conduction band of a polar crystal by a high-intensity, short optical pulse may gain enough energy to damage the lattice by initiating an ionizing avalanche. We discuss here other processes by which these conduction electrons may damage the lattice even before they gain enough energy to ionize their surroundings, specializing our calculations to the case of sapphire and ruby. First, we show that the energy that the conduction electrons absorb linearly from the optical beam is deposited almost immediately in the lattice without significant heating of the electrons. At electron densities ( $\sim 10^{16} \text{ cm}^{-3}$ ) and optical intensities ( $\sim 10^{10} \text{ W/cm}^2$ ) likely to exist at sapphire damage thresholds, this deposited energy is found to be of the order of what one might expect would be required to form a rupturing shock wave. We also show that the photo-excitation of both bound and unbound impurity levels is enhanced by the presence of conduction electrons, so markedly so for the former that the promotion of electrons into the conduction band may be significantly "bootstrapped," thereby increasing the optical absorption. The presence of conduction electrons and excited impurities in the expected numbers is likely to alter the refractive index significantly and affect thereby the focusing (self- or external) of the beam in a complicated way. For the simplest model these nonlinear index contributions would tend to produce repeated focal regions along the beam. Implications of these results for raising damage thresholds are discussed.

Key words: Crystals, electrons, optical damage, photo-absorption, photo-conductivity, photo-electrons, polar crystals, ruby, sapphire, self-focusing.

## 1. Introduction

The physical processes responsible for the bulk damage caused in various transparent crystals by short optical pulses (causing negligible electrostriction) have not yet all been identified. Here we argue that several processes not considered previously are likely to be important in the optical damage of inclusion-free polar crystals, especially sapphire and ruby. For their initiation, these processes would all seem to require on the order of  $10^{16}$  conduction electrons per cc to be present at the point of maximum optical intensity, a number widely suspected to be present in sapphire and ruby at peak intensities  $\sim 10^{10} \text{ W/cm}^2$  just below damage threshold. We will argue here that such densities of cold electrons can a) transfer damaging amounts of heat from the beam to the lattice; b) accelerate the rates of photo-excitation of bound and free impurity electron states, thus significantly increasing the supply of conduction electrons, possibly even in "avalanche"; and c) significantly change the local refractive index, possibly in a way which, in conjunction with the normal nonlinear index, could cause repeated beam focusing along its axis. In none of these processes do the electrons become hot enough ( $\sim 8 \text{ eV}$ ) to ionize the lattice, in contradistinction to the process suggested by previous workers [1-4]<sup>2</sup>.

<sup>1</sup> Work supported in part by the Joint Services Electronics Program (U. S. Army, Navy, and Air Force), under Grant No. AF-AFOSR-69-1622A, and in part by the Advanced Research Projects Agency through Air Force Cambridge Research Laboratories.

<sup>2</sup> Figures in brackets indicate the literature references at the end of this paper.

\* Presented at the ASTM Symposium on Laser Damage, Boulder, Colorado, 24-25 June 1970 and will be published in the Proceedings.

Hence, we will refer to them as "cold" conduction electrons. How the damage processes discussed here depend on crystal temperature, optical wavelength and pulse duration is a complex function of the energies and wavefunctions of the states of the impurities supplying and trapping conduction electrons, the electrons' effective mass(es), the longitudinal optical (L.O) phonon structure, and the electron-phonon coupling. Although only the latter two are fairly well known for ruby and sapphire, plausible hypotheses about the former lead one to single out the processes we propose as potentially important to damage. It would appear that reducing donor concentrations or increasing their electron binding energies might produce more damage-resistant crystals. However, if the conduction electron density were proportional to optical intensity (which appears not to be the case at such high intensities), it would tend to reduce self-focusing (or produce a net defocusing) and thereby lower damage thresholds. Other conclusions and suggested experimental checks of electron processes are mentioned in the final Section. In the following Section 2 we summarize the parameters and physical regimes we encounter in ruby and sapphire and we outline our rough criteria for when damage is expected. In Section 3 we define the approach we take for evaluating the required parameters and discuss difficulties with previous calculations of the conditions under which hot ionizing electrons might be produced. The calculations of the enhancement by conduction electrons of lattice heating and photo-excitation follow in Sections 4 and 5. Before proceeding, we first summarize our assessment of often-conflicting reports on photoconductivity in ruby and sapphire.

Hochuli [5] has measured the low-frequency photoconductivity at various wavelengths and temperatures of ruby and sapphire at optical intensities  $1 \sim 0.2$  to  $5 \text{ W/cm}^2$  and using applied voltages at frequencies zero Hz, 100 Hz, and 9.39 GHz. He found no essential differences in results for the two crystals. The observed conductivities (at  $5 \text{ W/cm}^2$ ) were  $4 \times 10^{-13}$ ,  $10^{-11}$ , and  $4.2 \times 10^{-8} (\text{ohm})^{-1}$ , respectively, at the above frequencies. Since all these frequencies are well below the electron collision frequency (which from the theory of Section 4 we estimate to be  $\sim 10^{14} \text{ rps}$ ), the wide variations in results indicate the magnitude of experimental pitfalls in any attempt to measure such low bulk conductivities. Anomalies at the two lower frequencies probably arise from surface effects, from the inability of electric contacts to inject charges into the crystal, and from space charge buildup. Therefore, the 9.39 GHz value, obtained in a microwave cavity with a small electron drift excursion amplitude (of the order of an Angstrom), is probably the most reliable. This conductivity was linear in the optical intensity within the range of observations. Its wavelength dependence suggested that the electrons were supplied from donor levels between 0.6 and 1.2 eV below the conduction band, in agreement with what one would conclude by studying the normal bulk conductivity variation with temperature at higher temperatures. The wavelength dependence also suggested more donor levels appearing around 5 eV. Although Hochuli was able to observe a Hall voltage, it did not vary when the light was turned on or off. The nominal Hall mobility value  $\mu = 0.052 \text{ cm}^2/\text{V sec}$  derived therefrom has nevertheless been used without question by other workers whenever a value was required in calculations. This value corresponds to a collision time  $\tau$  of  $4 \times 10^{-17} \text{ sec}$ , or an electron mean path of the order  $10^{-10} \text{ cm}$ , and must be considered unphysical, corroborating the difficulty of making electrodes on sapphire. Using the standard Frohlich theory of a conduction electron in a polar crystal adapted to the large coupling constant of sapphire [6], one estimates  $\tau$  (at room temperature) to be between  $10^{-14.4}$  and  $10^{-13.4} \text{ sec}$ , depending on where the effective band mass lies between  $1/10$  and  $10$  electron masses. Assuming a free electron mass for which  $\tau = 7 \times 10^{-15} \text{ sec}$  (and  $\mu = 12 \text{ cm}^2/\text{V sec}$ ), one would infer from Hochuli's microwave observations that he produced  $\sim 2 \times 10^8$  photo-electrons per cc with  $5 \text{ W/cm}^2$  of broadband Hg lamp exciting intensity. We see from this that  $10^{16}$  electrons per cc would very likely be excited near damage thresholds of  $10^{10} \text{ W/cm}^2$  provided that  $10^{16}$  donor levels per cc were occupied, a provision which is unknown.

Except possibly for the experiments of Belikova, et al. [7,8], other reported observations of photoconductivity in ruby appear to be plagued by surface and contact effects. Belikova, et al., observed the photoconductivity to be highly nonlinear with the (6943 Å) optical intensity  $I$  for intensities near  $10^{10} \text{ W/cm}^2$ . One can use our value of  $\tau$  above with their data to estimate very crudely (since their beam geometry was unspecified) that they were observing well over  $10^{16}$  electrons/cc at  $10^{10} \text{ W/cm}^2$  (provided that the electron recombination time was short compared with the optical pulse length). Belikova, et al., also observed optical emission bands near 2, 2.7, and 3 eV (they could not see below 2 eV) which are suggestive of some impurity level transitions. The foregoing is about all one can conclude about photo-electrons from existing data for ruby and sapphire.

## 2 Description of Electron Interactions

In studying the role of photo-excited electrons in crystal damage, we will constantly apply our formulae to the case of sapphire and ruby. The phonon structure of these two crystals are essentially identical, as are the low-intensity photoconductivities. Although distinct differences in damage behavior have been observed, the gross damage thresholds are statistically indistinguishable for sapphire and ruby. Therefore, most pertinent aspects of these two crystals can be studied together. For brevity, we shall refer hereafter only to sapphire, but shall intend our remarks to apply also to ruby unless stated otherwise. We shall also assume throughout that the optical beam wavelength is 6943 Å, that of the room temperature ruby laser.

A free electron gas of density  $10^{16} \text{ cm}^{-3}$  has a plasma frequency  $\omega_p \sim 6 \times 10^{12} \text{ rps}$  that is much lower than a) the optical beam frequency of interest  $\nu$  ( $2.71 \times 10^{15} \text{ rps}$ ), b) the phonon frequencies  $\omega_k$  ( $\sim 10^{14} \text{ rps}$ ), and c) typical electronic excitation frequencies ( $\sim 10^{16} \text{ rps}$ ).

We shall call a conduction electron "cold" when its energy is much less than interband energies and its wavelength is much longer than the scale of potential variations of the field lattice. Other electrons we will refer to as "hot". The time for cold electrons in the 1/40 to 3 volt range to equilibrate among each other by collisions at a density  $10^{16} \text{ cm}^{-3}$  is of the order of  $10^{-10}$  to  $10^{-13} \text{ sec}$  [9], much longer than the inverse electron-lattice collision time ( $\sim 10^{-14} \text{ sec}$  in ruby). Therefore, at least before any large ionizing avalanche occurs, the cold conduction electrons may be studied as independent particles, not interacting among themselves but interacting only with the fields and other particles in the crystal.

When a cold electron moves in a polar crystal such as ruby or sapphire, it is often called a "polaron." Its interactions with the crystal phonons are known to be well-described at room temperature and above by the Hamiltonian derived by Frohlich [10] and used by all previous workers in calculating electron motions leading to damage:

$$H_F = h_0 + v_F \quad (1)$$

where

$$h_0 = \frac{1}{2} [p - A(t)]^2 + \sum_k \omega_k a_k^\dagger a_k \quad (2a)$$

and

$$v_F = \sum_k C_k a_k e^{ik \cdot x} + \text{h.c.} \quad (2b)$$

Here  $p$  is the electron's momentum, and  $x$  the electron's position coordinates,  $a_k$  is the annihilation operation for a LO phonon of frequency  $\omega_k$ . Optical wavelengths are long enough so that the vector potential  $A(t)$  may be taken as a function of time only oscillating at a frequency  $\nu$ . We use dimensionless "polaron" units in which the effective band mass of the electron  $m_b$  is unity as is Planck's constant  $\hbar$ . All energies are measured in units of an effective LO phonon energy  $\hbar\omega_0$  ( $680 \text{ cm}^{-1}$  or  $980^\circ \text{K}$  for sapphire and ruby). Frequencies are measured in units of  $\omega_0$  ( $= 1.6 \times 10^{14} \text{ rps}$ ) so that  $\nu = 17$  for a  $6943 \text{ \AA}$  beam in sapphire. Lengths are measured in units of  $(\hbar/m_b \omega_0)^{1/2}$  which is  $8.5 \times 10^{-8} \text{ cm}$  for ruby if we take  $m_b$  to be the free electron mass  $m_0$ . Frohlich showed that in these units the coupling coefficients  $C_k$  are well approximated by  $V^{-1/3} \omega_0^{1/2} \epsilon_0^{-1/2} k^{-1}$  where  $V$  is the crystal volume,  $\epsilon_0$  is the dimensionless polaron coupling constant ( $\epsilon^{-1} - \epsilon_0^{-1}$ ) ( $\text{Ryd}'/\hbar\omega_0$ ). Here  $\text{Ryd}'$  is the Rydberg for an electron with mass  $m_0$ , and  $\epsilon$  and  $\epsilon_0$  are the optical and static dielectric constants (3.1 and 10). For  $m_b = m_0$ ,  $\epsilon \sim 3$  for ruby. In ruby an electron is hot if  $k$  is of order 10 or more (in polaron units). Hot conduction electrons have neither the simple forms of kinetic energy or lattice interaction energies found in eq (1) but obey complex equations in which exchange must be accounted for and which have never satisfactorily been approximated in usable form for a dynamic lattice. There would seem to be no way at present to make a reliable estimate of how strong an optical field would be required to produce enough interband electronic transitions (i. e., lattice ionization) to cause damage.

From the discussion of the previous section, it is evident that the electrons photo-excited (below damage thresholds) in ruby and sapphire crystals come from donor impurities to which they are bound initially with much less energy than the valence-conduction band gap energy ( $\sim 8 \text{ eV}$ ). The effects of these impurities on the supply and motions of conduction electrons, as well as on the excitation of the donors by conduction electrons, can be studied by considering the Coulomb interactions  $v_i$  between a conduction electron at  $x$  and the  $i^{\text{th}}$  particle of the  $\alpha^{\text{th}}$  impurity having charge  $eq_i^\alpha$  and located at  $x_i^\alpha$ .

$$v_i = e^2 \epsilon_s^{-1} \sum_{i,\alpha} q_i^\alpha / |x - x_i^\alpha| \quad (3)$$

where the electronic charge  $e$  is 4 in our polaron units, and is screened by the dielectric constant  $\epsilon_s$  appropriate to the frequencies of motions under consideration.

To deal with the elastic scattering of the electrons, one needs only the matrix element of eq (3) diagonal in the impurity's ground state. This gives an effective classical scattering potential seen by the conduction electron. To study inelastic scattering, we will assume that the impurities may be described by an unperturbed Hamiltonian  $h_i = \sum_\alpha h_{i\alpha}$  with "ionized" or unbound as well as bound electronic eigenstates. Calculations will therefore start from a total Hamiltonian  $H$  comprised of

Frohlich's Hamiltonian eq (1) (which describes cold electrons, phonons, and their interaction) plus the electron impurity interactions of eq (2) and with  $h_i$  determining impurity states

$$H = h_0 + h_i + v_p + v_i \quad (4)$$

We will assume that damage to the crystal occurs when the interactions  $v_p$  and  $v_i$  combined cause the conduction electrons to absorb an energy  $U$  per cubic centimeter with a short optical pulse that exceeds a threshold value  $U_0$ . That is, we shall strive to determine at what optical beam intensity we may expect

$$U \geq U_0 \quad (5)$$

Present evidence indicates that  $U_0$  is of order  $10^2$  to  $10^3$  eV/cm<sup>3</sup> for ruby and sapphire for 20 nsec pulses in a beam of order one mm diameter. A shock wave of this energy surrounding the beam would develop stresses on the order of the static yield stress. Obviously a large part of understanding optical damage in crystals entails developing an accurate theory of the amount of energy deposition required to produce enduring strains as a function of the amount and spatial and temporal distribution of this deposition. However, we shall content ourselves here with the above crude estimate for  $U_0$ .

### V. Approaches to the Calculation of Damage Thresholds

Previous treatments of the role of electrons in damage [1,4] started from Frohlich's Hamiltonian eq (1) and sought to calculate the optical intensity at which electrons would gain enough energy  $u$  to excite an avalanche of interband transitions. The expected energy  $u$  of an electron in the optical field was estimated from the equation

$$\frac{du}{dt} = R_{fe} - R_{ef} \quad (6)$$

where  $R_{fe}$  is the average rate at which the optical field does work on the electron and  $R_{ef}$  is the average rate at which the excited electron radiates phonons, i.e., transfers its energy to the lattice. Previous treatments have all taken for  $R_{fe}$  the usual linear conductivity loss per electron with reasonable order of magnitude estimates from eq (1) for the optical conductivity (or electron collision rate). However, they have made approximations for, or statements about,  $R_{ef}$  that are not directly based on a quantum average of the appropriate operator. Waserman [1] took for  $R_{ef}$  the rate at which an electron having a Maxwellian distribution would lose energy to a cooler lattice in the absence of the optical field ( $A = 0$ ). He predicted breakdown intensities orders of magnitude above those actually observed. Sverre, et al. [4], used for  $R_{ef}$  the approximate rate at which an electron would lose energy to the lattice starting from a momentum eigenstate  $|p\rangle$  for which  $\hbar p^2 = u$  also in the absence of the optical field. His predicted thresholds also exceeded observed thresholds by over two orders of magnitude. We feel it is quite probable that a precise evaluation of the spectral energy distribution of an electron obeying eq (1) would show that the electrons do in fact remain too cool to ionize impurities or the lattice at optical fields below damage thresholds. In the next section we show that, indeed, collisions with phonons dominate an electron's motion. We have checked that it follows rigorously from eq (1) that, to lowest order in the optical intensity and coupling parameter  $\alpha$ , an electron's expected kinetic energy is simply the sum of its coherently oscillating energy plus  $\hbar T/2$  where  $T$  is the ambient lattice temperature. The coherent energy is very much smaller than  $\hbar T$  for optical intensities of interest. Therefore, we now proceed to examine whether cold electrons may not mediate the deposition of damaging amounts of energy in a sapphire lattice.

As we mentioned in the previous section, our approach will be to calculate the beam intensity at which the energy  $U$  deposited per unit volume in the lattice from the optical field via the electrons exceeds a threshold value  $U_0$ . If the maximum optical beam energy per unit area is  $S$ , then

$$U = \kappa_y S \quad (7)$$

where  $\kappa_y$  is the absorption per unit length of an optical beam of frequency  $y$ . Following FHIP [6], we write the quantum expectation value of the amplitude of an electron's coordinate at frequency  $y$  as  $\text{Re } E e^{i(y - \omega_c)t} / (-\omega_c^2 + y^2)$  when the electron is in an optical electric field  $\text{Re } E e^{i\omega_c t}$ . With this definition we have



$$\chi_v = (\omega_p^2 / \epsilon) \text{Im}[\epsilon^2 - \chi_v]^{-1} \quad (8)$$

where  $\epsilon$  is the wavelength of the light in the crystal  $\epsilon = 2\pi$  and  $\omega_p$  is the electron plasma frequency (in units of  $\omega_0$ ). In cgs units  $\omega_p^2 = 4\pi e^2 n / m_b$  with  $n$  being the number density of electrons.

The evaluation of  $\chi_v$  falls naturally into two parts: first, the determination of the rate at which a single conduction electron takes energy from the field (and delivers it to the lattice) by a calculation of  $\chi_v$ , and second, the estimation of the number density  $n$  of these electrons. We consider these two questions, respectively, in the following two sections.

#### 4. Optical Response of Single Electron

We examine first an electron's optical response in the case that it is affected only by electron-phonon interactions as described by Frohlich's Hamiltonian eq (1) with coupling parameters appropriate to sapphire. We then find that, at least at room temperatures and above, collisions with impurities are relatively less important. When the electron response is linear in the applied field for a given lattice temperature, we may use the determination of  $\chi_v$  by Fittip who calculated the quantum expected value of the electron position to first order in the optical field. Their expression is exact for all temperatures at small coupling ( $a < 1$ ) and gives an accurate solution even when  $a \sim 3$  as for ruby. In this case it shows that, for  $\gamma = 17$ , both the real and imaginary parts of  $\chi_v$  are much less than  $\gamma^2$  so that we need only calculate  $\text{Im}\chi_v$  to estimate the absorption constant. (The  $\text{Re}\chi_v$  can of course be determined from  $\text{Im}\chi_v$  by Kramers-Kronig relations.)

$$\text{Im}\chi_v = \frac{2a\omega_p^2 \beta^{3/2} \sinh(\beta v/2)}{3 \sinh(\beta/2)} \left(\frac{v}{w}\right)^3 \int_0^\infty \frac{\cos(vu) \cos u \, du}{[u^2 + a^2 - b \cos(vu)]^{3/2}} \quad (9)$$

Here  $v$  and  $w$  are parameters to be chosen from a variational principle.  $a^2 = \beta^2/4 + R\beta \coth(\beta v/2)$ ;  $R = (v^2 - w^2) / (w^2 v)$ ; and  $b = R\beta \sinh(\beta v/2)$ .

In the weak coupling limit  $v = w = 3$ ,  $R = b = 0$  and  $a = \beta/2$ . Then the integral can be evaluated exactly in terms of modified Bessel functions. At temperatures much lower than the Debye temperature ( $\beta$  large) this result reduces to

$$\text{Im}\chi_v = 2a(v-1)^{3/2}/3 : a < 1, \beta \gg 1, v > 1. \quad (10)$$

For  $a = 3$  and  $\gamma = 17$ , this is 8. The leading correction to eq (10) for finite temperatures multiplies it by  $(1 + \beta^{-1})$ , increasing it by 30% at room temperature ( $\beta = 3.3$ ).

When  $a = 3$ , the variational principle gives  $v = 3.4$  and  $w = 2.55$  in the zero temperature limit (6). Using these parameters with  $\beta = 3.3$  gives  $R = 0.22$ ,  $a = 1.866$  and  $b = 5.53 \times 10^{-3}$ . We have evaluated eq (9) numerically for these parameters and have obtained  $\text{Im}\chi_v = 15$ . We have also evaluated eq (9) at frequencies in the neighborhood of  $\gamma = 17$  and found that, as in eq (9),  $\text{Im}\chi_v$  varies slowly with  $\gamma$ . Therefore, electron transients associated with the rise and fall of even picosecond optical pulses are very small, and it is a good approximation in practice to assume that at any instant the electron's motion is the same as for a purely sinusoidal field of amplitude appropriate to the intensity at that instant. The fast response of the electron's motion, as evidenced by the nonresonant character of  $\chi_v$ , together with the knowledge that, at intensities of interest, the electron is gaining negligible energy (staying "cold"), implies that the absorbed energy is being passed on essentially instantaneously to the phonons via the coupling eq (2b). Therefore, it is valid to obtain the rate of deposition of energy in the lattice by determining the rate at which the electrons absorb energy from the optical beam, and we return to this problem.

When a room temperature correction is made to  $v$  and  $w$ , we guess that, as for small  $a$ , the result is raised by around 30% so that the Frohlich model may be taken to yield

$$\text{Im}\chi_v \sim 20 \quad (11)$$

for a ruby laser beam driving an electron of band mass equal to a free electron mass in ruby or sapphire at room temperature. The main uncertainty in eq (11) comes from the uncertainty in the effective band mass  $m_b$ .  $\text{Im}\chi_v$  varies roughly as  $m_b^{1/2}$ .

If the temperature goes higher than the phonon energy but is still small compared with  $\nu$ , then eq (9) yields

$$\text{Im} \chi_y \sim 4\alpha \nu^{1/2} / (3\beta) \quad ; \quad \alpha \ll 1, \quad 1 \ll \beta^{-1} \ll \nu, \quad (12)$$

showing that the heated lattice causes the electrons to absorb even more light. Note that the "Q" of the electron's oscillation,  $\nu^2 / (2 \text{Im} \chi_y)$ , is of order 7 for our estimate eq (11), showing that indeed the optical frequency is much larger than the effective electron collision frequency as we assumed.

One can see at this point that absorption by conduction electrons may cause damage, for, if the electron density were  $10^{16} \text{ cm}^{-3}$  at an optical intensity of  $10^{10} \text{ W/cm}^2$  (which the evidence outlined in Section 1 suggests as a conservative estimate), and if eq (11) were valid, then  $\omega_p \sim 10^{-3}$  and eq (8) gives  $\chi_y \sim 0.012 \text{ cm}^{-1}$ . For a 30 nsec pulse this absorption would deposit 40.1 peV/cc in the lattice, somewhat less than the value  $U_0$  expected to cause damage. However, Belikova, et al. [7], gave convincing evidence that the electron density is increasing very rapidly with optical intensity at these levels, an occurrence which we expect for reasons given in the following section. Before considering factors which affect the electron density, however, we consider contributions other than those of the linear response eq (9) to electron damping.

First, the question arises as to whether there are significant intensity-dependent corrections to the electron response at the optical frequency as represented by eq (9). (Responses at harmonic frequency multiples do not contribute to the average work done by the optical field on the electrons and so we need not consider these here.) There are two types of nonlinear corrections to eq (9): first, those arising from the nonlinear reactions of the phonons on the electron, and, second, those arising from the intensity-dependent deviations of the momentum distribution of electrons from a thermal distribution. We have estimated both effects by expanding the quantum expression for the expected electron position (and velocity) to the third order in the electric field. We have found that both effects tend to diminish the optical absorption from its linear response value, a result expected on the physical grounds that electrons of high energy interact less with the optical phonons than do low-energy electrons. For both corrections the natural dimensionless expansion parameter is  $(k_0 r_0)^2$  where  $k_0$  is the wavevector of an electron having energy  $\hbar\nu$  and  $r_0$  is the classical amplitude of a free electron oscillating in the applied optical field. In our case this parameter is  $\sim I(\text{W/cm}^2) \times 10^{-13}$ . Since optical intensities have not yet been observed to approach even  $10^{11} \text{ W/cm}^2$  before damage, we conclude that the nonlinear corrections to eq (9) are too small to be of importance in present considerations.

Next, we see why, under conditions of interest here, phonon scattering of conduction electrons dominates scattering by ionized and un-ionized lattice impurities. For each conduction electron there is in the lattice a heavy positive ion whose charge is shielded roughly by the static dielectric constant of the lattice ( $\epsilon_0 \sim 10$ ). The linear absorption by  $10^{16}$  electrons per cc in such a two-component plasma at room temperature is  $\sim 10^{-6}$  per cm [1]. This is so small compared with phonon effects that one can readily appreciate that even if  $10^{19}$  per  $\text{cm}^3$  of electrically neutral scattering centers were added to the lattice, one would not expect them to scatter electrons as effectively as do phonons at room temperature and above. This predominance of phonon scattering at or above room temperature has been observed in various ways even in crystals whose electron-phonon coupling is much smaller than in ruby and sapphire [12]. Having estimated the optical response of a single conduction electron, we now proceed to consider how their numbers are affected by their interactions with lattice impurities.

### 5. Conduction Electron Interactions with Impurities

From incomplete existing absorption [13] and luminescence [8] data, it is evident that sapphire has a complex impurity level structure with energy differences ranging up to at least 3 eV. Light of any single optical wavelength, such as 6943 Å, will not be resonant with a significant fraction of the bound-bound transitions and, of course, will only excite transitions to the conduction band from bound levels within 1.8 eV of the band edge. If, however, the light became effective in exciting a large fraction of the bound-bound transitions, then cascade transitions of electrons into the conduction band from levels lying more than 1.8 eV below the band edge might dominate direct photo-excitation. We shall now show that, at conduction electron densities  $\sim 10^{16} \text{ cm}^{-3}$ , the light does become so effective in exciting bound-bound transitions with which it is not resonant that cascade photo-excitation may become important in increasing the conduction electron density near optical damage intensities. These non-resonant transitions are possible because the conduction electrons readily absorb the difference in energy  $\nu - \omega_{ba}$  between an absorbed photon and the energy of transition between the upper and lower states  $|b\rangle$  and  $|a\rangle$ . We now show that the rate  $R_{ab}$  for a typical impurity to make such a transition, multiplied by a reasonable impurity density ( $\sim 10^{19} \text{ cm}^{-3}$ ), may exceed the total direct photo-excitation rate, and thereby initiate cascade ionization of impurities.

To calculate the rates  $R_{ab}$  it is convenient to re-express the interaction of eq (3) as a Fourier transform (the impurity index  $a$  is now omitted since we are considering only one impurity):

$$v_i = \sum_{\underline{k}} v_{\underline{k}} e^{i\vec{k} \cdot \vec{x}} \quad (13)$$

where  $v_{\underline{k}}$  is the impurity operator  $4\pi e^2 V^{-1} \epsilon_s^{-1} k^{-2} \sum_j \exp i\vec{k} \cdot \vec{r}_j$  and  $V$  is a fiducial interaction volume. The sum is confined to the bound impurity electrons as only electronic transitions will be considered. For the transitions of interest we may take  $\epsilon_s$  to be the optical dielectric constant  $\epsilon$ . With the form eq (13) it is a straightforward matter to re-derive the quantum "Golden Rule" for calculating transition rates but with an unperturbed Hamiltonian  $h_0 = \frac{1}{2}(\vec{p} - A_0 \cos \omega t)^2$  instead of  $\frac{1}{2}p^2$ . To lowest order in the electron-impurity interaction, the rate for an electron to scatter from momentum state  $|\underline{p}\rangle$  to  $|\underline{p} + \underline{k}\rangle$  while the impurity goes from  $|a\rangle$  to  $|b\rangle$  is

$$\Gamma(\underline{p} \rightarrow \underline{p} + \underline{k}; a \rightarrow b) = 2\pi |\langle b | v_{\underline{k}} | a \rangle|^2 \sum_{n=-\infty}^{\infty} \delta(k^2/2 + \underline{p} \cdot \underline{k} + \omega_{ba} + n\nu) \cdot [J_n(k \cdot \underline{r}_0)]^2 \quad (14)$$

where we have retained the terms for  $n$ -photon emission and absorption for future comparison with the  $n = 1$  term that we are now considering. In the polaron units used here the classical electron oscillation amplitude  $r_0$  equals  $E/\nu^2$ , where the real amplitude  $E$  of the optical electric field equals the amplitude in esu divided by  $E_0 = (\omega_0^2/c) (\hbar m_b/\omega_0)^{1/2}$ . For our parameters  $E$  equals (the field in V/cm)  $\div (1.24 \times 10^6)$ . The Bessel function coefficients  $J_n$  in eq (14) are the exact amplitudes for absorbing (or emitting)  $n$  optical photons in the process. Their arguments are of order  $10^{-13}$  I(W/cm<sup>2</sup>) and so the approximation  $J_n(x) \sim (x/2)^n/n!$  is accurate here. Consider now the rate  $r_{ab}$  for the impurity interacting with one electron in the optical field to make a transition from a state  $|a\rangle$  to a state  $|b\rangle$ , for which  $\omega_{ba} < \nu$ . In terms of the rate eq (14)

$$r_{ab} = \sum_{\underline{p}, \underline{k}} f(\underline{p}) \Gamma(\underline{p} \rightarrow \underline{p} + \underline{k}; a \rightarrow b) \quad (15)$$

where  $f(\underline{p})$  is the initial conduction electron distribution and only the  $n = 1$  term in  $\Gamma$  is needed. To evaluate  $r_{ab}$  it remains to estimate the dependence of the matrix elements of  $v_{\underline{k}}$  on  $\underline{k}$ . We shall use the "dipole approximation" in which  $\langle b | \exp i\vec{k} \cdot \vec{r}_j | a \rangle \sim i\vec{k} \cdot \langle b | \vec{r}_j | a \rangle$ . For definiteness we will assume that the impurity is spherically symmetric so that  $|\sum_j \vec{k} \cdot \langle b | \vec{r}_j | a \rangle|^2 = k^2 X_{ba}^2$  where  $X_{ba}$  is the dipole matrix element of the impurity transition. Finally, before evaluating eq (20), we average over all directions of  $\underline{r}_0$  so that the  $J_1^2$  term becomes  $(kE/2\nu)^2/3$ . The  $n = 1$  contribution to the sum over  $\underline{k}$  in eq (15) is then

$$r_{ab} = V^{-1} 16\pi e^4 (r_0^2/12) \epsilon^{-2} X_{ab}^2 \sum_{\underline{p}} L(\underline{p}) f(\underline{p}) \quad (16a)$$

where

$$L(\underline{p}) = \int_{K_m - p}^{K_m + p} dk k^{2n-1}/p. \quad (16b)$$

Generally  $K_{m1} \approx [p^2 + 2(\nu - \omega_{ba})]^{1/2}$  is much larger than the magnitude of  $p$  allowed in  $f(\underline{p})$ . In this case, it is sufficiently accurate to approximate eq (16b) by

$$L \sim 2[2(\nu - \omega_{ba})]^{1/2} \quad (17)$$

and we see that the impurity excitation rate is essentially independent of the initial small conduction electron momentum  $\underline{p}$ . Since  $\sum_{\underline{p}} f(\underline{p}) = 1$ , this fact makes the sum in eq (16a) trivial. The total rate  $R_{ab}$  for an impurity to absorb a photon is  $r_{ab}$  times the number of conduction electrons in the interaction volume  $V$ . It is convenient to express  $R_{ab}$  in terms of a photon absorption cross-section  $\sigma_{ab}$  which equals  $R_{ab} \div$  (the incident photon flux). Recalling that  $2\nu r_0^2$  is numerically  $10^{-13}$  I(W/cm<sup>2</sup>), we have from eq (15) for sapphire

$$\sigma_{ab} \sim 7.5 \times 10^{-11} I X_{ab}^2 \epsilon^{-2} \nu^{-1} (\nu - \omega_{ba})^{1/2} \rho_e \quad (18)$$

in polaron units where the electron density  $\rho_e$  is  $6.15 \times 10^{-22}$  times the number of electrons per cc  $\rho$ .

To see the importance of the transition cross-section eq (18) relative to direct photo-excitation, we estimate the density of impurities  $N_i \text{ cm}^{-3}$  that would be required to attenuate the optical beam more than does the direct photo-excitation process. Of course, the latter attenuation is not known, but it must be less than the total attenuation in sapphire, and that is less than  $10^{-2}$  per cm. For argument, suppose that direct photo-excitation causes less than  $10^{-3}$  per cm optical attenuation (it probably causes much less). For our estimate, let us assume in eq (18) that  $X_{ab}^2 \sim 1/\omega_{ab}$ ,  $\omega_{ab} \sim 8$ , and  $I = 10^{10} \text{ W/cm}^2$  and  $\sigma = 10^{16}$  as in previous examples. This gives  $\sigma_{ab} \sim 10^{22} \text{ cm}^2$  so that  $N_i \sim 10^{19}$  impurities per cc would be required to make these conduction-electron-mediated impurity transitions attenuate the optical beam by  $10^{-3}$  per cm. Considering all the kinds of dislocations and foreign ions which might take part as impurities in this process, we feel that it is not unreasonable that such an impurity density could exist. Of course, there are so many order-of-magnitude estimates of unknown quantities in the foregoing that the result can only be considered as suggestive of a kind of process that must be considered as competitive with other possibilities at this time. However, the experimental observation of a rapidly increasing dc photoconductivity near damage thresholds [7] does suggest a "bootstrap" process such as the above by which conduction electrons can create more of their kind, even before they become so energetic as to ionize the lattice.

We have examined the enhancement of the single-photon bound-free photo-excitation transitions that arise from eq (14), and have estimated that excitation cross-section also to be of order  $10^{-22} \text{ cm}^2$  under the same conditions. This is probably less than the cross-section for direct photo-excitation. If multi-photon excitation is important in producing electrons, then the higher  $n$  terms of eq (14) probably dominate direct absorption near damage levels. The expansion parameter in eq (14) is of order  $10^{-13} \text{ l(W/cm}^2\text{)}$ , whereas it is  $\sim 10^{-17}$  for direct multi-photon absorption.

## 6. Focusing Effects

In a region of the crystal in which conduction electrons have been excited there is a change in the refractive index  $\delta n$  given by

$$\delta n = -\omega_p^2/v^2. \quad (19)$$

At a density  $10^{16} \text{ cm}^{-3}$ , electrons (with free electron band mass) have a plasma frequency of  $10^{12} \text{ Hz}$ , which gives  $\omega_p/v \sim 0.0023$  and  $\delta n \sim 5.3 \times 10^{-6}$ . This index change is comparable to that required to self-focus a one milliradian gaussian beam. If the electron density were proportional to the optical intensity  $I$ , and this index change were produced when  $I = 10^{10} \text{ W/cm}^2$ , then the index change would constitute a second order nonlinear index (often written  $n_2 E^2$ ) whose nonlinear coefficient  $n_2$  would be  $-2 \times 10^{-13} \text{ esu}$ . This is negative and an order of magnitude larger than what one would guess is the intrinsic nonlinear index of the bound electrons in sapphire. However, we suspect that the electron density is increasing much more rapidly than  $I$  at high intensities [7] and so the effect of the index of eq (19) is not simple. Furthermore, impurity electrons which are excited to bound states more than  $\sim$  below the band edge, such as by the process discussed in the previous section, have an increased polarizability and would tend to cancel the effect eq (19) of conduction electrons.

Suppose the net effect of impurity transitions were to produce a negative and highly nonlinear refractive index change, as would be the case if the conduction electron effect eq (19) dominated. Then there would be strong self-defocusing of a beam in regions of very high intensity, but only the intrinsic self-focusing index would be operative in regions of smaller intensity. This would evidently result in successive regions of high intensity along the beam as each effect produces in turn a focusing tendency that brings the other effect into dominance. Damage tracks in sapphire and other materials consist of a sequence of damage bubbles that are suggestive of such a process. However, we have not calculated the spacing of the successive high-intensity regions on the basis of some reasonable model to see whether there is any possible correspondence between these speculations and observation.

## 7. Discussion

Although there are alternate explanations for the behavior of damage tracks observed in sapphire [14], it seems likely that self-focusing is occurring and playing a role in the damage. (It is curious that the appearance, lengths, and positions of damage tracks differ between ruby and sapphire [14].) If self-focusing is occurring, it makes especially difficult the determination of the actual optical intensities at which the material ruptures, and this in turn lends an extra uncertainty to the parameters we have used in discussing the role of conduction electrons in damage. Probably the most promising way to determine more precisely what the electrons' role may be is to determine the parameters of these conduction electrons below damage intensities. It would be especially desirable to have reliable dc photoconductivity measurements between the intensities  $5 \text{ W/cm}^2$ , the highest used by Hochuli [7], and  $10^{10} \text{ W/cm}^2$ , the lowest used by Belikova, et al. [7], in their measurements. With the high light intensities available with lasers, it may now be possible to excite enough electrons to obtain a

meaningful Hall effect. Perhaps the time decay of photoconductivity and luminescence after an exciting pulse could be observed and yield information on carrier lifetimes, trapping times, etc. Unfortunately, the important and pervading parameter – the effective mass in the conduction band (and its anisotropy) – appears to be extremely difficult to determine experimentally.

Should the photo-excited electrons be found to play significant roles in damage, such as those we have discussed, then it may be possible to fabricate more damage-resistant sapphire and ruby. For example, if self-focusing is presently instrumental in damage, then it might be reduced by adding donor impurities that produce a linear photoconductivity at high intensities and thus reduce the total nonlinear index via the index change of eq (19). On the other hand, those donors that give a highly nonlinear photoconductivity and a sudden production of high electron densities that result in rupture by photo-absorption may perhaps be eliminated from the crystals or compensated by other additives. In any case, it is evident that the availability of high-intensity laser sources will greatly facilitate the study of the conduction bands and impurity levels in very weakly photoconducting materials such as sapphire and ruby.

## 8. References

- [1] A. Wasserman, "A mechanism for damage in solids by intense light," *Appl. Phys. Letters* 10, 132-133 (1967).
- [2] V. A. Pashkov and G. M. Zverev, "Destruction of ruby and leucosapphire crystals by strong laser radiation," *Soviet Phys. -JETP* 24, 516-518 (1967).
- [3] E. A. Sviridenkov, "Mechanism of damage of ruby by laser radiation," *Soviet Phys. -Solid State* 9, 1917-1918 (1968).
- [4] G. M. Sverev, T. N. Mikhailova, V. A. Pashkov, and N. M. Solov'eva, "Mechanisms of destruction of ruby and leucosapphire crystals by powerful laser radiation," *Soviet Phys. -JETP* 26, 1053-1057 (1968).
- [5] Urs E. Hochuli, "Photoconductivity in ruby and sapphire," *Phys. Rev.* 133A, 468-471 (1964).
- [6] R. P. Feynman, R. W. Hellwarth, C. K. Iddings, and P. M. Platzman, "Mobility of slow electrons in a polar crystal," *Phys. Rev.* 127, 1004-1017 (1962). Hereinafter referred to as FHIP.
- [7] T. P. Belikova and E. A. Sviridenkov, "Photoconductivity of ruby when strongly irradiated by a ruby laser," *JETP Letters* 3, 257-259 (1966).
- [8] T. P. Belikova, A. N. Savchenko, and E. A. Sviridenkov, "Optic breakdown in ruby and related effects," *Soviet Phys. -JETP* 27, 19-23 (1968).
- [9] L. Spitzer, Jr., *Physics of Fully Ionized Gases* (Interscience Publishers, New York, 1956).
- [10] H. Frohlich, "Theory of electrical breakdown in ionic crystals," *Proc. Phys. Soc. (London)* A160, 230-241 (1937).
- [11] V. I. Perel and G. M. Eliashberg, "Absorption of electromagnetic waves in plasma," *Soviet Phys. -JETP* 14, 633-637 (1962).
- [12] R. H. Bube, *Photoconductivity of Solids* (John Wiley and Sons, New York, 1960).
- [13] N. V. Beardsley, *Proceedings of the Infrared Information Symposia*, Volume 1, No. 2, 47-53 (1956).
- [14] C. R. Giuliano and L. D. Hess, "Laser-induced damage in ruby and sapphire," in these *Proceedings*.

DOCUMENT CONTROL DATA - R&D

(If the report is classified, the following information must be entered when the overall report is classified)

1. ORIGINATOR: **Alperant Company, Research Labs. Div.**  
**3011 Malibu Canyon Road**  
**Malibu, California 90265**

2. REPORT SECURITY CLASSIFICATION  
**Unclassified**  
 2a. GROUP

3. REPORT TITLE

**DAMAGE THRESHOLD STUDIES IN LASER CRYSTALS: EXPERIMENTAL AND THEORETICAL RESULTS IN RUBY AND SAPPHIRE**

4. DISTRIBUTION STATEMENT (If distribution is unlimited)

**Scientific Interim**

5. AUTHOR(IES) (If the author is not known, enter "Unknown")

**Concetto R. Giuliano LaVerne D. Hess**  
**Robert W. Hellwarth Gerald R. Rickel**

6. REPORT DATE  
**July 1970**

7a. TOTAL NO. OF PAGES  
**48**

7b. NO. OF REFS  
**1**

8. CONTRACT OR GRANT NO.

**F19628-69-C-0277 ARPA Order No.**  
**8693-n/a-n/a 1434**

9. ORIGINATOR'S REPORT NUMBER(S)

**Semiannual Report No. 2**

10. DOWNGRADING

**61101D**

11. DOWNGRADING

**n/a**

9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)

**AFCRL-70-0437**

12. DISTRIBUTION STATEMENT

**1- This document has been approved for public release and sale; its distribution is unlimited.**

13. SUPPLEMENTARY NOTES

**This research was supported by Advanced Research Projects Agency**

14. SPONSORING MILITARY ACTIVITY

**AF Cambridge Research Labs (OPL)  
 L.G. Hanscom Field  
 Bedford, Massachusetts 01730**

15. ABSTRACT

In this report the results of a number of experiments are presented as well as a summary of the theoretical work. Bulk damage thresholds for several ruby and sapphire samples from different sources are presented. The problem of surface damage is discussed, and qualitative comparisons between entrance and exit surface damage are made. Differences between the gross characteristics of bulk damage in ruby and sapphire are presented and discussed. The dependence of damage threshold on  $TiO_2$  doping and optical pumping is presented. The unexpected results are discussed and further experiments proposed. The theoretical treatment deals with processes by which "cold" conduction electrons may damage the lattice before they gain enough energy to ionize their surroundings. It is shown that the energy that the conduction electrons absorb linearly from the optical beam is deposited almost immediately in the lattice and is of sufficient magnitude to form a rupturing shock wave. It is also shown that the photoexcitation of impurity levels is enhanced by the presence of conduction electrons. The presence of conduction electrons and excited impurities is likely to alter the refractive index significantly and affect the focusing (self- or external) in a complicated way. Implications of these results for raising damage thresholds are discussed.

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Bulk damage						
Crystals						
Damage thresholds						
Electrons						
Lasers						
Mode control						
Optical Pumping						
Ruby						
Sapphire						
Self focusing						
Surface damage						